

Chitosan/Siloxane Hybrid Polymer: Synthesis, Characterization and Performance as a Support for Immobilizing Enzyme

Grazielle S. Silva, Pedro C. Oliveira, Domingos S. Giordani and Heizir F. de Castro*

Escola de Engenharia de Lorena, Universidade de São Paulo, CP116, 12602-810 Lorena-SP, Brazil

O polímero híbrido derivado de siloxano e quitosana foi obtido pela técnica sol-gel, tendo como precursor o tetraetilortossilicato (TEOS). O suporte híbrido obtido foi modificado quimicamente com epícloridrina e utilizado para imobilizar lipase de *Burkholderia cepacia*. O híbrido SiO₂-quitosana deu origem a uma nova estrutura macromolecular na qual as partículas inorgânicas encontram-se dispersas em escala nanométrica na matriz orgânica e ligadas à matriz por meio de ligações covalentes. Foi realizado um estudo comparativo entre a lipase livre e a imobilizada quanto à influência do pH e temperatura, parâmetros cinéticos e estabilidade térmica. O pH ótimo para a atividade máxima de hidrólise da lipase imobilizada foi de 6,1, enquanto que para a lipase livre foi de 7,0. A temperatura ótima permaneceu em 50 °C mesmo depois da imobilização. Os perfis de estabilidade térmica indicaram que o processo de imobilização foi favorável à estabilização da enzima e o derivado epóxi SiO₂-quitosana foi cerca de 30 vezes mais estável que a lipase livre a 60 °C.

A hybrid polymer derived from siloxane and chitosan was obtained by sol-gel technique using tetraethoxysilane (TEOS) as a precursor. The hybrid support was chemically modified with epichlorohydrin and used to immobilize lipase from *Burkholderia cepacia*. The hybrid SiO₂-chitosan formed new macromolecular structure in which the inorganic particles are dispersed at the nanometer scale in the organic host matrix and bounding through covalent bonds. A comparative study between free and immobilized lipase was provided in terms of pH, temperature, kinetic parameters and thermal stability. The pH for maximum hydrolysis activity shifted from 7.0 for the soluble lipase to 6.1 and the optimum temperature remained at 50 °C after immobilization. The patterns of heat stability indicated that the immobilization process provided the stabilization of the enzyme and the epoxy SiO₂-chitosan derivative was almost 30-fold more stable than soluble lipase at 60 °C.

Keywords: chitosan, hybrid matrix, lipase, immobilization

Introduction

Enzyme immobilization usually provides, in addition to the desired reuse of the biocatalyst, unexcelled advantages such as product separation and continuous operation.¹ Moreover, immobilization may be used to improve other enzyme features, such as increasing the activity,² decreasing inhibitions,³ modulating selectivity and specificity⁴ or improving the enzyme behavior in synthetic processes.⁵ Particularly for lipase,⁶ the immobilization state is required to attain high product yield so it is not surprise that its immobilization has been the object of intensive investigation.⁶ Several commercially immobilized preparations are available,

such as *Candida antarctica* lipase B immobilized onto polyacrylate type matrix, available under the name of Novozym 435® (Novozymes) or Chirazyme L-2® (Roche). Some lipases are also available in the cross-linked forms, such as cross-linked enzyme crystals (CLECs) offered by Altus Biologics Inc. However, for some applications, the relatively high cost of those biocatalysts associated with the usage of an expensive carrier material, becomes unfeasible for further exploitation. Therefore, the development on less expensive immobilizing procedure is need to emerge into relative low margin applications such as interesterification of fats when compared to the relative high margin applications, for example enantioselective synthesis of pharmaceutical intermediates.⁶

The organic-inorganic sol-gels have received significant interest because the incorporation of organic polymers in

*e-mail: heizir@dequi.eel.usp.br

the inorganic sol-gel can lead to new composite materials possessing the properties of each component that would be useful in particular applications.⁷ This method has been considered as outstanding to synthesize a significant number of materials with high degree of homogeneity and purity at a molecular level with extraordinary physical and chemical properties.⁸ The sol-gel reaction involves the hydrolysis of silica precursors and condensation of the resulting hydroxyl groups to form a nano-structure. It has been widely used in the fields of mesoporous materials, membrane materials and intelligent hybrid hydrogel.⁹⁻¹² One simple method is mixing organic compounds with a metal alkoxide, such as tetraethoxysilane (TEOS).

It has been reported that the inorganic nanocomposite is formed *in situ* in a biopolymer solution by the self-organization of sol particles generated in the course of hydrolysis of TEOS and following polycondensation reactions into a porous three-dimensional network in the bulk solution. During the sol-gel process the inorganic mineral is deposited in the organic compound matrix forming hydrogen bonding between organic and inorganic phases. To increase the solubility, methanol or ethanol is usually added.¹³ Some organic/inorganic hybrids on the basis of different inorganic precursors and organic compounds, such as cellulose,¹² carrageenan¹³ and polyvinylalcohol¹⁴ have been reported. Incorporation of organic polymers, especially those with amino or amide groups, allows the formation of molecular hybrids often stabilized by strong hydrogen bonding.¹⁵ Moreover, chemical additives can be used to improve the process and the attainment of materials with better mechanical properties, porosity control and hydrophilic/hydrophobic balance.¹⁶

Several applications have been already developed for this kind of hybrid materials particularly in the biotechnological field. The dispersed inorganic particles impart the properties of hardness, brittleness and transparency, whereas density, free volume and thermal stability depend on the organic host polymer.¹⁷⁻¹⁹ Hydrolysis and condensation reactions are basically responsible for polymerization of the inorganic precursors.

Using this methodology, polymers such as chitosan are able to form hybrids with silica.¹⁵ This macromolecule, derived chemically by deacetylation of chitin, the second most abundant biopolymer in nature close to cellulose, has widely been assumed to be a cheaper and versatile sorbent for transition metal ions and organic substances through the coordination and/or reaction sites composed of the amino ($-\text{NH}_2$) and hydroxy ($-\text{OH}$) groups anchoring on chitosan chains.²⁰ As a matter of fact silica-chitosan possesses a highly porous microstructure and has been shown to be a superior support for immobilizing enzymes.¹ Moreover, it

is inexpensive, non-toxic, hydrophilic, biocompatible and biodegradable.²¹

Thus, this work assesses the performance of a silica-chitosan hybrid matrix synthesized by sol-gel process, using TEOS as a precursor to immobilize lipase from *Burkholderia cepacia*. This enzyme was chosen due to its potential previously identified to synthesize important products, such as biodiesel and monoglycerides.²²⁻²³ The properties of the support (SiO_2 -chitosan) and immobilized derivative were evaluated by X-ray diffraction, Fourier transform infrared spectroscopy (FTIR) and thermogravimetry (TG). The influence of the temperature and pH on the activity of the biocatalysts was determined using a surface response methodology. Under the established conditions, the kinetic behavior of the immobilized lipase was also determined. The results were compared with those attained by the free lipase.

Experimental

Materials

Burkholderia cepacia (Lipase PS) was purchased from Amano Enzyme Inc. (Nagoya, Japan) and used without further purification. Chitosan flaks (C3646-Sigma) with a degree of deacetylation of 85% and tetraethoxysilane (TEOS) were obtained from Sigma-Aldrich Chemicals Co. (Milwaukee, WI, USA). Epichlorohydrin, hydrochloric acid (minimum 36%) and polyethylene glycol (PEG, molecular weight-1500) were supplied by Reagen (Rio de Janeiro, RJ, Brazil). Commercial olive oil (low acidity) was purchased in a local market. All other chemicals were of analytical grade.

Support synthesis and activation

SiO_2 -chitosan was prepared by the hydrolysis and polycondensation of tetraethoxysilane according to the methodology reported by Paula *et al.*¹⁶ with slight modifications as briefly described. An initial solution of chitosan (0.125 g) and ethanol (5 mL) in water (20 mL) was heated at 60 °C under agitation, followed by addition of 1.0 mL of concentrated HCl. The solution was stirred for 12 h for total chitosan dissolution. After this period, 5 mL of TEOS were added under agitation for 40 min and the product was transferred to micro wells of tissue culture plates (disc shape) and kept at 25 °C until complete gel solidification (formation of an interpenetrated network of SiO_2 -chitosan). Then, the material was ground in a ball mill and classified to attain particles with 0.308 mm of diameter ($-40/+60$ MESH Tyler standard sieves). Activation of the

hybrid particles was carried out with epichlorohydrin at 2.5% (m/v) and pH 7.0 for 1 h at room temperature, followed by exhaustive washings with distilled water.

Lipase immobilization onto epoxy SiO₂-chitosan particles

Activated epoxy SiO₂-chitosan particles were soaked into hexane under stirring (100 rpm) for 1h at 25 °C. Then, excess hexane was removed and powder lipase preparation was added at a ratio of 1:4 g of enzyme *per* g of support. PEG-1500 as lipase stabilizer was added together with the enzyme at a fixed amount (5 mg g⁻¹ of support). Lipase-support system was maintained in contact for 16 h at 4 °C under static conditions. The immobilized lipase derivatives were filtered (nylon membrane 62HD from Scheiz Seidengazefabrik AG, Thal Schweiz, Switzerland) and thoroughly rinsed with hexane. Hydrolytic activities of free and immobilized lipase derivatives were assayed by the olive oil emulsion method according to the modification proposed by Soares *et al.*²⁴ One unit (U) of enzyme activity was defined as the amount of enzyme that liberates 1 μmol of free fatty acid *per* min under the assay conditions. The results were expressed in activity units *per* g of solid (free enzyme preparation or immobilized derivative).

Determination of optimal enzymatic activities and kinetic parameters

Enzymatic activities for free and immobilized lipases as a function of temperature and pH were investigated according to a five-level-two-factor central composite rotatable design (CCRD) with three replications at the center point. The activities were assayed by the hydrolysis of olive oil emulsion at a fixed proportion oil/water 1:1.²⁴ The pH values were achieved using appropriate phosphate buffer solutions (0.1 mol L⁻¹). Results from the experimental design were analyzed using Statistica version 5 (StatSoft Inc., USA). The statistical significance of the regression coefficients was determined by Student's test; the second order model equation was determined by Fischer's test and the proportion of variance explained by the model obtained was given by the multiple coefficient of determination, R².

The influence of substrate concentration on the hydrolytic activities was also analyzed in the olive oil hydrolysis assay varying the proportion of oil in the emulsion from 10 to 50%. Michaelis-Menten constant (K_m) as the concentration of substrate at which half of the maximum reaction rate (V_{max}) is reached was calculated with aided by computational program Enzfitter version 1.05 published by Elsevier-Biosoft, 1987. In all cases, enzyme activity was measured as the initial reaction rate (0-5%

hydrolysis) to avoid the possible inhibition that might take place due to the appearance of reaction products.

Thermal stability

Soluble (1.0 mL) and immobilized derivative (0.1 g) were incubated in the presence of 1 mL buffer phosphate pH 6.5 (100 mmol L⁻¹) at 60 °C for different time intervals. Samples were removed and assayed for residual activity as previously described,²⁴ taking an unheated control to be 100% active. The rate of denaturation (k_d) and half-life time (t_{1/2}) were calculated by equations 1 and 2, respectively.

$$A_{in} = A_{in0} \exp(-k_d t) \quad (1)$$

$$t_{1/2} = \ln 0.5 / -k_d \quad (2)$$

Characterization

Fourier transform infrared spectroscopy (FT-IR, Perkin-Elmer, model spectrum GX FT-IR system) was used for studying chemical bonds between hybrid support and lipase. Micrographs were obtained with a scanning electron microscopy (SEM, LEO1450VP, Schott Zeiss from Brazil). X-ray diffraction patterns were collected on a XRD 6000 X-ray diffractometer Shimadzu (Shimadzu from Brazil), using CuK radiation source, with 2θ angle varying from 15-80°. Thermal stability and weight loss profiles were determined using a thermo gravimetric analysis-TG apparatus (TGA-50 Shimadzu-thermogravimetric analyzer). All TGA measurements were accomplished in nitrogen atmosphere and examined over the range of 25 to 1000 °C, with a heating rate of 10 °C min⁻¹. The typical sample amount was 10.00 ± 0.5 mg.


Results and Discussion

Synthesis and characterization of SiO₂-chitosan matrix


Figure 1 is a hypothetical representation of the synthetic route used for the preparation of hybrid polymer by sol-gel process, involving three steps:²⁵ (i) hydrolysis of the precursor (SiO₂) in acidic solution; (ii) polycondensation of the formed monomers to produce oligomers arranged as sol particles and (iii) formation of SiO₂-chitosan hybrid matrix by cross-linking of the sol particles leading to a sol-gel transition.

The product of the polycondensation reaction is a typical inorganic glass type material having hydroxyl groups on the surface. The chitosan is adsorbed on silica particle via hydrogen bonds between sylanol groups in

step 1 - hydrolysis



step 2 - polycondensation

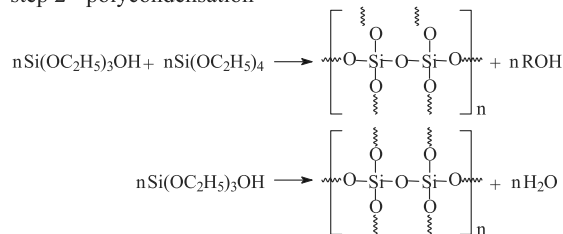

step 3 - matrix formation

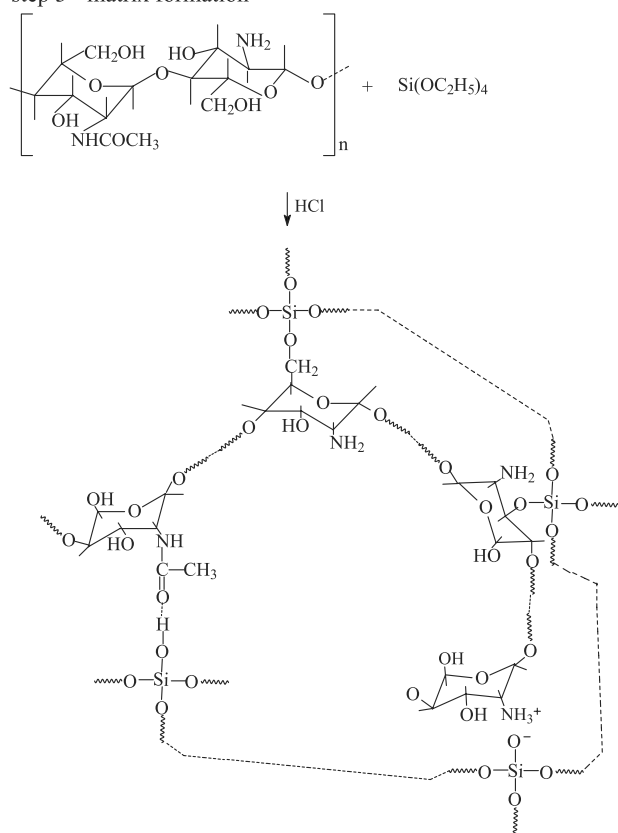


Figure 1. Hypothetic representation of SiO_2 -chitosan matrix formation (Adapted from reference 25).

the silica network and amide and oxy-groups of chitosan, ionic bonds between chitosan amino groups and silyanol groups as well as covalent bonds in result of esterification of chitosan hydroxyl-groups of silyanol groups of silica network.^{25,26} The SiO_2 -chitosan hybrid forms new molecular structures containing not only organic groups, but also inorganic nano-silica particles. These inorganic particles are dispersed in the chitosan matrix, forming network organic-inorganic hybrid. SiO_2 -chitosan is transparent, vitreous, brittle and homogeneous (Figure 2).

The infrared spectrum (Figure 3) shows bands at 1110 to 1000 cm^{-1} corresponding to Si–O–R asymmetric

stretching and hydroxyl groups (3600-3200 cm^{-1}).²⁷ Other characteristic bands were observed at 950 cm^{-1} (Si–O–Si axial deformation), 810 cm^{-1} (Si–O–Si axial deformation) and 600 cm^{-1} (Si–O–Si angular deformation).²⁸

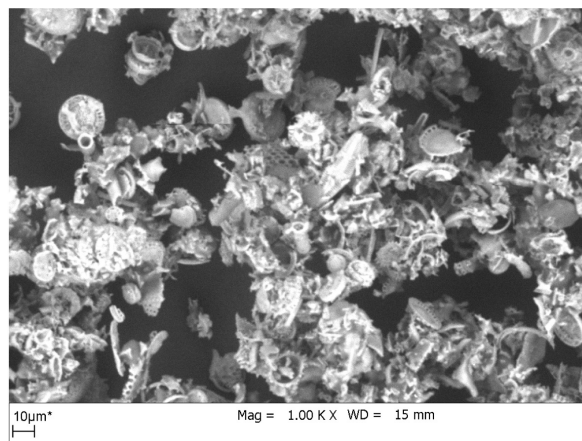


Figure 2. SEM micrograph for SiO_2 -chitosan.

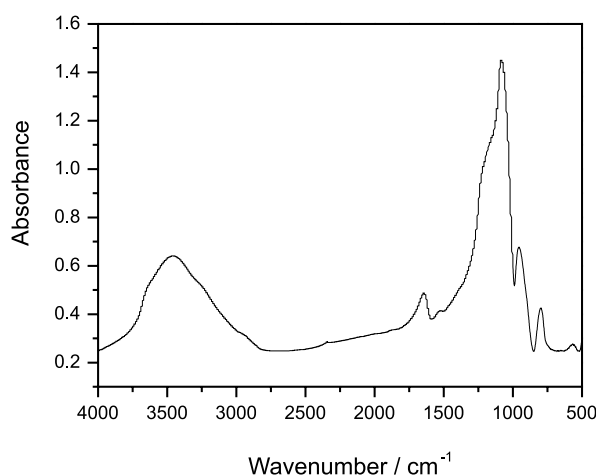


Figure 3. FTIR spectra for the SiO_2 -chitosan.

The XRD displays peaks of low intensity and expressive width, indicating a predominantly amorphous structure of the hybrid composite (Figure 4), with one halo centered around 23° (2θ). According to Ogawa *et al.*²⁹ pure chitosan could be arranged in noncrystalline, hydrated crystalline and anhydrous crystalline forms which is represented by peaks around 11.7° , 14.2° and 23° , respectively. The disappearance of these two crystalline peaks in hybrid composite indicates the prominence of chitosan amorphous structure, influencing directly the structure of hybrid composite.

SiO_2 -chitosan thermal behavior was evaluated by TGA as can be seen in Figure 5. The initial weight loss (26%) was observed around 155°C and can be attributed to loss of adsorbed water on the surface of chitosan and side

product of subsequent condensation of Si–OH groups.²⁷ The second weight loss (29%) was observed at 275 °C due to the decomposition of low molecular weight species. Thermal decomposition was marked in the region of 275 °C up to 800 °C (around 40%). In this range of temperature probably occurred the dehydration of the saccharide rings, depolymerization and decomposition of the units of the organic polymer as well as the inorganic part of the hybrid.^{30,27} The higher temperature values for the first stage of decomposition observed for support compared to the first stage decomposition temperature of the pure chitosan (60 °C),³¹ indicates that the formation of the hybrid of SiO₂-chitosan was successful.

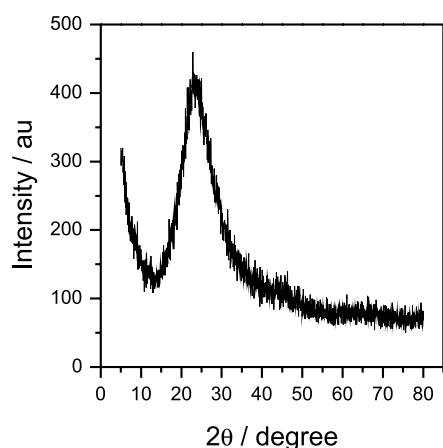


Figure 4. X-ray diffractogram for SiO₂-chitosan.

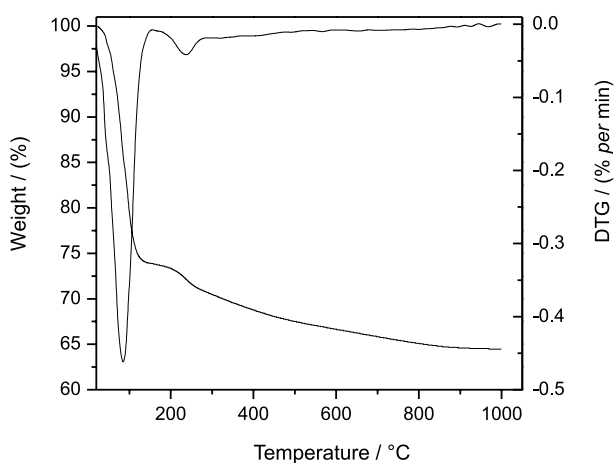


Figure 5. Thermal analysis for SiO₂-chitosan.

Morphological characteristics of the immobilized derivative

SiO₂-chitosan was submitted to activation procedure involved the incorporation of aldehyde groups on the surface of the support by reacting with the hydroxyls of SiO₂-chitosan, aiming to render adequate functional groups to the covalent binding with the enzyme.

Epichlorohydrin reacts directly with the hydroxyl groups of chitosan generating epoxide groups which are able to link to the enzyme. Some reticulations can also be present, but it will depend on the degree of deacetylation of chitosan as well as concentration of activating agent and reaction time (Figure 6).³²⁻³⁴ PEG1500 (not shown) was used for improving activity of the biocatalyst as previous described.³⁵

The epoxy SiO₂-chitosan support was used to immobilize *Burkholderia cepacia* (lipase PS) by covalent binding. Typically 0.25 g of powder lipase *per g* of dry support was found to be sufficient to attain satisfactory retention of enzyme on the support (30 ± 0.5%) and immobilized derivative having high activity (1620 ± 58 units g⁻¹ support).

The efficiency of the methodology in relation to the lipase incorporation on the support was also assessed by infrared spectroscopy. This technique is used to detect the presence of covalent bonds in molecules, based on the principle that each type of covalent bond has a characteristic absorption wavelength represent as an upward peak on a charted spectrum.²⁸ Figure 7 shows spectra for both free and immobilized lipase.

Free enzyme displayed a typical spectrum of proteins with bands associated to their characteristic amide group (CONH). In this case, in the range from 1700 to 1600 cm⁻¹, there is a amide I band due to the double bond CO stretching, the CN stretching and NH bending.²⁸

For the immobilized derivative, a slight additional bands in the spectrum at 1600 cm⁻¹ was observed, indicating that the covalent bond between the enzyme and support occurred (NH bending). Bands corresponding to carboxyl deformation (2800 and 1500 cm⁻¹) disappeared, which demonstrated that the characteristic functional groups of the lipase were covalently bond on the groups inserted in the support.²⁸

Diffraction of the X-ray information data on the activated support (epoxy SiO₂-chitosan) and immobilized derivative is shown in Figure 8. The diffractogram obtained from the epoxy SiO₂-chitosan shows peaks of low intensity and expressive width, indicating a predominantly amorphous structure of the hybrid composite.¹⁴ The immobilization procedure resulted on support structure modifications which clearly indicated insertion of crystalline regions into the SiO₂-chitosan that can be associated with the presence of the enzyme. As can be seen in the inserted box in Figure 8, free lipase exhibits XRD with peaks intense and narrow which is typical for high crystalline structure of protein. The insertion of this crystalline structure of the lipase on the immobilized derivative confirmed that the immobilization procedure was successfully achieved.

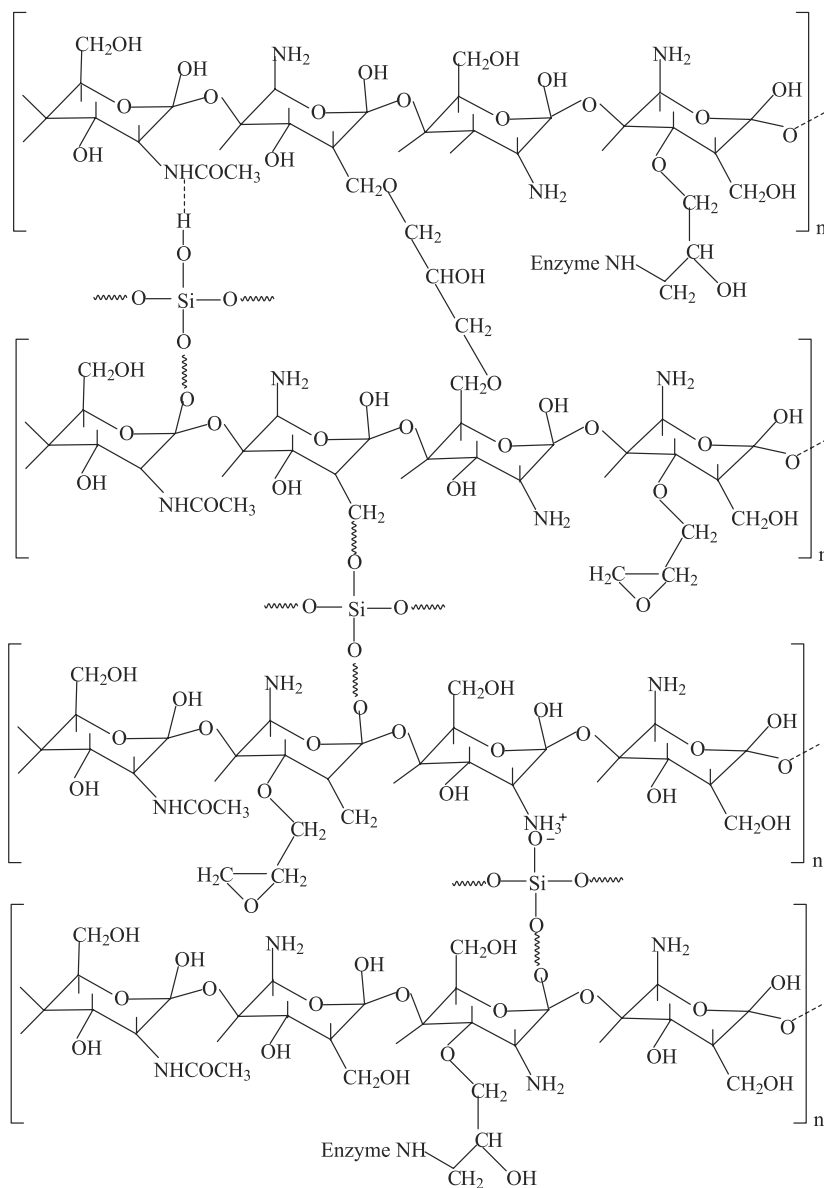


Figure 6. Proposed mechanism for SiO₂-chitosan activation with epichlorohydrin and immobilization step.

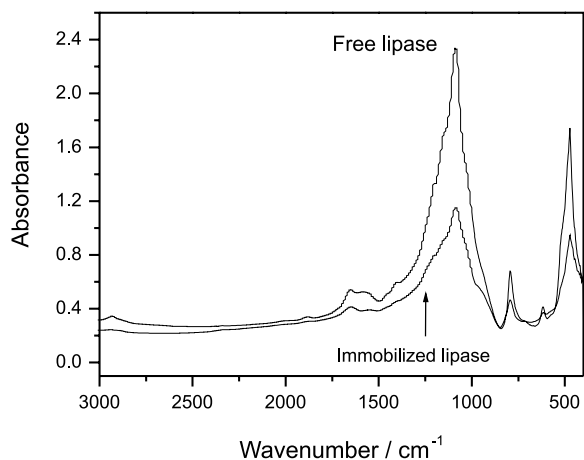


Figure 7. FTIR spectra for free and immobilized lipase.

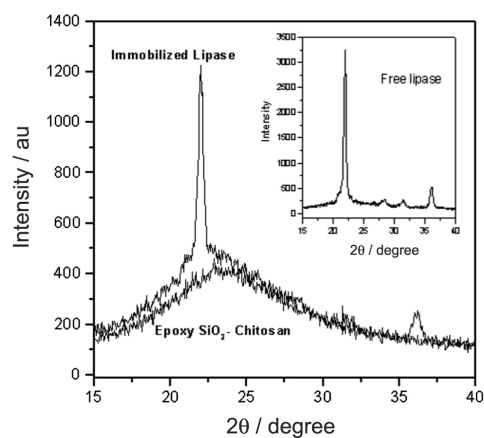


Figure 8. X-ray diffractograms for epoxy SiO₂-chitosan and immobilized derivative. Inserted box shows diffractogram for free lipase.

Biochemical and kinetics properties of the immobilized derivative

The influence of the variables pH and temperature on the hydrolytic activities for free and immobilized lipase was assessed by two level factor central composite rotatable design (CCRD) with three replications at the center point taking the hydrolytic activities as response variable. The experimental matrix and the results are shown in Table 1.

Table 1. Experimental design and results according to the central composite “2²+star”

Run	Variable		Hydrolytic activity / (U g ⁻¹)	
	pH (X ₁)	Temperature / (°C) (X ₂)	Free Lipase	Immobilized lipase
1	6.5	40	13215	1177
2	8.5	40	16593	1365
3	6.5	60	15307	1984
4	8.5	60	9361	1235
5	7.5	50	32748	1489
6	6.1	50	9801	1998
7	8.9	50	14023	1507
8	7.5	36	20291	1257
9	7.5	64	20189	1356
10	7.5	50	35181	1410
11	7.5	50	34500	1301
12	7.5	50	33381	1458

For the free lipase, activity values were 9361 to 35181 U g⁻¹ and immobilized lipase values varied from 1177 to 1997 U g⁻¹. The highest values were attained at pH 7.5 and temperature 50 °C (assay 10) for the free lipase and pH 6.1 and temperature 50 °C (assay 6) for the immobilized lipase.

The individual effects and interaction of factors (pH and temperature) in hydrolytic activity for free and immobilized lipases were estimated with aid of Statistica 5.0. Table 2

Table 2. Estimated effects, standard errors and Student's *t* test for the hydrolytic activity of free and immobilized lipase on epoxy SiO₂-chitosan using the 2² central composite “2²+star”

Variable	Free lipase			Immobilized lipase on SiO ₂ -chitosan		
	Effect	Standard Error	p	Effect	Standard Error	p
Mean	33953	± 547	0.000*	1414	± 41	0.000*
X ₁ (Linear)	850	± 773	0.352	-314	± 58	0.012*
X ₁ (Quadratic)	-23274	± 865	0.000*	293	± 65	0.020*
X ₂ (Linear)	-1321	± 773	0.186	204	± 58	0.039*
X ₂ (Quadratic)	-14943	± 865	0.000*	-153	± 65	0.101
X ₁ X ₂	-4663	± 1093	0.024*	-469	± 82	0.011*

*significant at 95% confidence level; X₁ and X₂ represent the variables pH and temperature, respectively.

displays the estimative of the effects of the variables, standard error and *p*-values.

Based on a 95% confidence level, models and each term were tested to be significant using Fisher's statistical test for analysis of variance (ANOVA). Predict values for models indicated that the regression was significant at 95% confidence level without lack of fit (*p* > 0.10). Results are described in Table 3 (free lipase) and Table 4 (immobilized derivative).

The models were checked by the determination coefficient and values (*R*² > 0.9055) indicated that the sample variation of 90.55% for hydrolytic activities is attributed to the independent variables and less than 10% of the total variations are not explained by the model. Thus, the equations were considered adequate to describe hydrolytic activity as a function of study variables and were used to plot the response surfaces as shown in Figures 9a and 9b.

The response surface for free lipase (Figure 9a) showed a top corresponding to a temperature of 50 °C and pH 7.5. For the immobilized lipase, saddle-shaped response surface was obtained (Figure 9b), within a maximum point corresponding to a temperature of 50 °C and pH 6.1.

The shift of optimal pH for immobilized lipase has been reported for different lipase sources and support types.^{33,36} Generally, immobilized lipases on polycationic supports shift its optimum pH to the acidic range. Huang *et al.*³⁷ reported that pH optimum for immobilized lipase from *C. rugosa* onto chitosan nanofibrous membrane shifted slightly from 7.7 to 7.5 when compared with the free one. In this study, a similar behavior was observed.

Under these optimal conditions, the kinetic parameters were determined for each lipase preparation. Figure 10 displays the curve profile for hydrolytic activities as a function of substrate concentration expressed in fatty acids molarity varying from 372 to 1860 mmol L⁻¹. Results showed that both lipase preparations obeyed the Michaelis-Menten equation, indicating that in the studied range, no inhibition by the reaction product was detected.

Table 3. Analysis of variance (ANOVA) for the model that represents the hydrolytic activity of the free lipase PS as a function of pH (X_1) and temperature (X_2)


Source	Sum of Squares ($\times 10^3$)	Degree of Freedom	Mean Square ($\times 10^3$)	F	p
X_1	1446	1	1446	1209	0.352
X_1^2	866326	1	866326	724645	0.000*
X_2	3491	1	3491	2919	0.186
X_2^2	357117	1	357117	298715	0.000*
X_1X_2	21739	1	21739	18184	0.024*
Lack of fit	24251	3	8084	6762	0.075
Pure Error	3586	3	1196		
Total SS	1097	11			

*significant at 95% confidence level; x_1 and x_2 represent the variables pH and temperature, respectively.

Table 4. Analysis of variance (ANOVA) for the model that represents the hydrolytic activity of the immobilized lipase as a function of pH (X_1) and temperature (X_2)

Source	Sum of Squares ($\times 10^3$)	Degree of Freedom	Mean Square ($\times 10^3$)	F	p
X_1	197384	1	197383	29079	0.012*
X_1^2	137706	1	137706	20287	0.020*
X_2	83351	1	83350	12279	0.039*
X_2^2	37220	1	37219	5483	0.101
X_1X_2	219820	1	219820	32384	0.011*
Lack of fit	54153	3	18051	2659	0.221
Pure Error	20363	3	6787		
Total SS	787081	11			

*significant at 95% confidence level; X_1 and X_2 represent the variables pH and temperature, respectively.

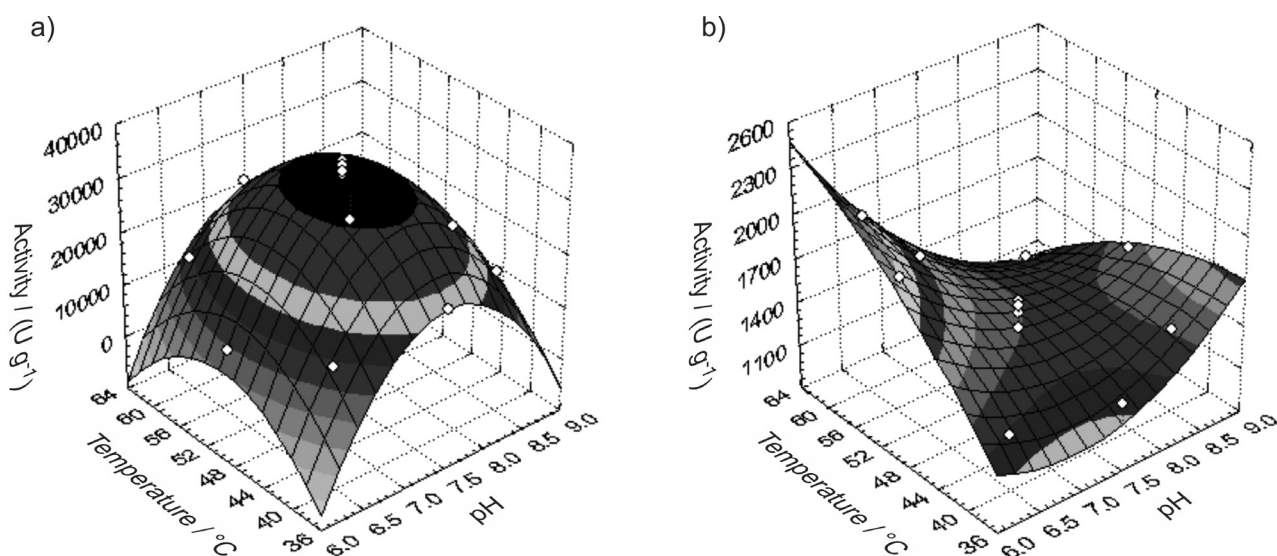**Figure 9.** Surface responses for the hydrolytic activity of the *Burkholderia cepacia* lipase in the free form (a) and immobilized on epoxy SiO_2 -chitosan (b) as a function of the variables pH and temperature according to the fitted mathematical models.

The apparent value of K_m for the immobilized lipase (819 mmol L^{-1}) was almost three times higher than that for the native enzyme (334 mmol L^{-1}) and the maximum

reaction rate (V_{\max}) were $16268 \text{ U g}^{-1} \mu\text{mol g}^{-1} \text{ min}^{-1}$ and $1921 \mu\text{mol g}^{-1} \text{ min}^{-1}$ for the free and immobilized lipase samples, respectively.

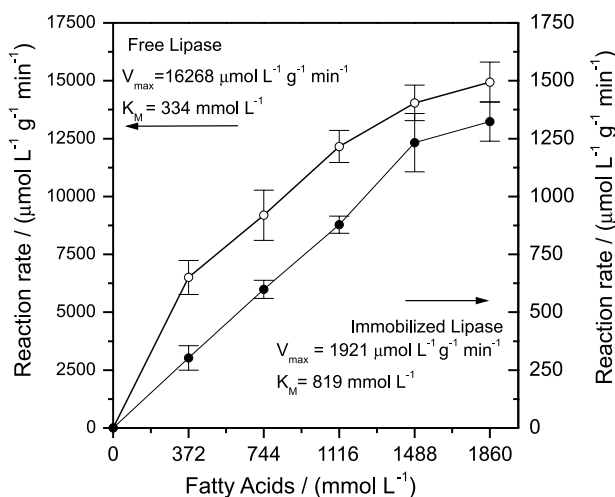


Figure 10. Hydrolytic activities for free and immobilized lipase on epoxy SiO₂-chitosan as a function of the substrate concentration (expressed in total fatty acids content in olive oil/water emulsions).

The kinetic values (K_m and V_{max}) indicate a change in affinity of immobilized enzyme to substrate. Changes in the kinetic parameters are found to be dependent on the enzyme source, kind of support, immobilization method and enzyme-support interactions.³⁸ In this work, K_m value for the immobilized lipase is higher than that of free lipase, which means the loss of affinity of lipase from substrate. A similar result involving increase in the K_m value of lipase after immobilization has been reported in the literature.³⁹ This increment after immobilization might either be due to structural changes in the enzyme induced by the applied immobilization procedure, or due to the use of epichlorohydrin as the activating agent. Moreover, the interactions of enzyme-support and diffusion resistance of carrier can be promoted by the lower accessibility of the substrate to the active sites of the immobilized enzyme.

Stability tests

Experiments were performed to determine the thermal deactivation constants (k_d) and the half-life time for free and immobilized lipase under thermal effect at 60 °C and results are displayed in Figure 11. Patterns of heat stability indicated that the immobilization process tends to stabilize the enzyme. In this case, half-life time ($t_{1/2}$) of the enzyme is shown to be inversely proportional to the rate of denaturation (k_d). The half-life time ($t_{1/2}$) is the time which takes for the activity to reduce to a half of the original activity.

Under these conditions, the immobilized lipase exhibited higher stability against heat than the soluble form. While the free enzyme was practically inactivated after 1 h incubation at 60 °C, the immobilized lipase preserved

about 40% of its original activity. Inactivation constants (k_d) and half-life ($t_{1/2}$) for both free and immobilized lipases were calculated, respectively as $k_d = 9.6 \text{ h}^{-1}$ ($t_{1/2} = 0.07 \text{ h}$) and $k_d = 0.33 \text{ h}^{-1}$ ($t_{1/2} = 2.1 \text{ h}$) indicating a raise of thermal stability near 30 fold when compared to free enzyme. Thermal stability upon immobilization is the result of molecular rigidity and the creation of a protected microenvironment.

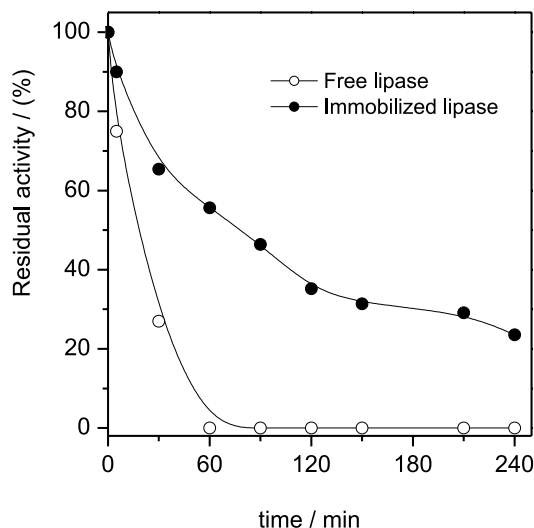


Figure 11. Thermal inactivation for free lipase (o) and epoxy SiO₂-chitosan immobilized lipase (●). Experiments were carried out in 0.1 mol L⁻¹ phosphate buffer pH 6.5 at 60 °C.

These results were also confirmed by running TG analysis which also allows determining the temperature range at which a heated sample undergoes a major conformational change by means of monitoring the thermal weight change profile as well as parameters for thermal stability of support and free and immobilized lipase. The results of such analysis are shown in Table 5.

The free lipase shows two peaks in mass change, the first at 127 °C (loss of water) and the second at 382 °C attributed to the decomposition of stabilizing agents present in the lipase preparation.⁴⁰ On the other hand, the immobilized lipase shows an increase in the temperature of the first stage of decomposition (174 °C), attributed to the covalent bond of the biocatalyst on the hybrid matrix. The discrete increase in the temperature of the second stage (397 °C) took place by the additional cross linking degree after the activation step. These results indicate that upon immobilization, the thermal profile for the lipase derivative shifted towards higher temperatures because of a strong interaction between enzyme and hybrid matrix, which enhanced the conformational stability of the native form.

To better illustrate the catalytic properties observed for the *Burkholderia cepacia* immobilized onto

Table 5. Thermogravimetry data for support and immobilized derivative

Sample	Step	Temperature / (°C)	Mass loss / (%)
Epoxy SiO ₂ -chitosan	1 st	162	10
	2 nd	537	20
Free lipase	1 st	127	2
	2 nd	382	15
	3 rd	546	22
Immobilized lipase	1 st	174	14
	2 nd	397	21
	3 rd	517	24

Table 6. Biochemical and kinetic properties for the free and immobilized lipase PS on SiO₂-chitosan

Parameter	Free Lipase	Immobilized Lipase
Optimum pH	7.5	6.1
Optimum Temperature / (°C)	50	50
Half-life time (t _{1/2}) at 60 °C / h	0.07	2.1
Kinetic Parameters	K _m / (mmol L ⁻¹)	334
	V _{max} / (U g ⁻¹)	16267
		1921

epoxy-SiO₂-chitosan, the biochemical and kinetic properties of free and immobilized lipase are summarized in Table 6.

Conclusions

Epoxy SiO₂-chitosan proved to be an attractive and efficient matrix to immobilize lipase due to its physical and chemical properties. The use of techniques such as X-ray diffraction and FTIR confirmed incorporation of the enzyme onto the support matrix. Experimental design data showed the significant influence of pH and temperature in hydrolytic activity of free and immobilized lipase. Values of K_m found for both lipase preparations indicated that immobilization process reduced the affinity of enzyme-substrate; however the k_d value indicated an increase of thermal stability of lipase. These results showed the potential of the epoxy SiO₂-chitosan matrix to immobilize lipases, particularly lipase PS. Moreover easiness of support synthesis and immobilization procedure, justify the importance of the evaluation of morphological and mechanical properties to obtain suitable carriers.

Acknowledgments

The authors are grateful for the financial support provided by FAPESP (Fundação de Amparo à Pesquisa do Estado de São Paulo) and CNPq (Conselho Nacional de Desenvolvimento Científico e Tecnológico), Brazil.

References

- Guisan, J. M. In *Immobilization of Enzyme and Cells*, Guisan, J. M., ed.; 2nd ed.; Humana Press: Totowa, 2006, ch. 1.
- Christensen, M. W.; Andersen, L.; Husumb, T. L.; Kirkb, O.; *Eur. J. Lipid Sci. Technol.* **2003**, *105*, 318.
- Luckarift, H. R.; *J. Liq. Chromatogr. Relat. Technol.* **2008**, *31*, 1568.
- Mateo, C.; Palomo, J. M.; Fernandez-Lorente, G.; Guisan, J. M.; Fernandez-Lafuente, R.; *Enzyme Microb. Technol.* **2007**, *40*, 1451.
- Bornscheuer, U. T.; Kazlauskas, R. J.; *Hydrolases in Organic Synthesis: Regio- and Stereoselective Biotransformations*, 2nd ed.; Wiley-VCH: Weinheim, 2005, ch 5.
- de Castro, H. F.; Zanin, G. M.; de Moraes, F. F.; Sá-Pereira, P. In *Enzimas em Biotecnologia-Produção, Aplicações e Mercado*; Bon, E. P. S.; Ferrara, M. A.; Corvo, M. L., eds.; Interciência: Rio de Janeiro, Brasil, 2008, ch. 6.
- Zhou, Z.; Ruan, J.; Zou, J.; Zhou, Z.; *J. Univ. Sci. Technol. Beijing* **2008**, *15*, 290.
- Nocun, M.; Cholewa-Kowalska, K.; Laczka, M. S.; *J. Mol. Struct.* **2009**, *938*, 24.
- Addamo, M.; Augugliaro, V.; Paola, A. D.; Garcia-Lopez, E.; Loddò, V.; Marci, G.; *Thin Solid Films* **2008**, *516*, 3802.
- Pappas, G. S.; Liatsi, P.; Kartsonakis, I. A.; Danilidis, I.; Kordas, G.; *J. Non-Cryst. Solids* **2008**, *354*, 755.
- Seckin, T.; Koytepe, S.; Ibrahim, A. H.; *Mater. Chem. Phys.* **2008**, *112*, 1040.
- Xie, K.; Zhang, Y.; Yu, Y.; *Carbohydr. Polym.* **2009**, *77*, 858.
- Shchipunov, Y. A.; *J. Colloid Interface Sci.* **2003**, *268*, 68.
- Santos, J. C.; Paula, A. V.; Nunes, G. F. M.; de Castro, H. F.; *J. Mol. Catal. B: Enzym.* **2008**, *52*, 49.
- Zou, Y.; Xiang, C.; Sun, L.-X.; Xu, F.; *Biosens. Bioelectron.* **2008**, *23*, 1010.
- Paula, A. V.; Moreira, A. B. R.; Braga, L. P.; de Castro, H. F.; Bruno, L. M.; *Quim. Nova* **2008**, *31*, 35.
- Kataoka, K.; Nagao, Y.; Nukui, T.; Akiyama, I.; Tsuru, K.; Hayakawa, S.; *Biomaterials* **2005**, *26*, 2509.
- Li, J.; Srinivasan, S.; He, G. N.; Kang, J. Y.; Wu, S. T.; Ponce, F. A.; *J. Cryst. Growth* **2008**, *310*, 599.
- Zhou, Z.; Cui, L.; Zhang, Y.; Yin, N.; *Eur. Polym. J.* **2008**, *44*, 3057.
- Krishnapriya, K. R.; Kandaswamy, M.; *Carbohydr. Res.* **2009**, *344*, 1632.
- Luo, X. -L.; Xu, J. -J.; Zhang, Q.; Yang, G. -J.; Chen, H. -Y.; *Biosens. Bioelectron.* **2005**, *21*, 190.
- Freitas, L.; Da Rós, P. C. M.; Santos, J. C.; de Castro, H. F.; *Process Biochem.* **2009**, *44*, 1068.
- Moreira, A. B. R.; Perez, V. H.; Zanin, G. M.; de Castro, H. F.; *Energy Fuels* **2007**, *21*, 3689.
- Soares, C. M. F.; de Castro, H. F.; Moraes, F. F.; Zanin, G. M.; *Appl. Biochem. Biotechnol.* **1999**, *77*, 745.

25. Rashidova, S. S.; Shakarova, D. S.; Ruzimuradov, O. N.; Satubaldieva, D. T.; Zalyalieva, S. V.; Shpigun, O. A.; Varlamov, V. P.; Kabulov, B. D.; *J. Chromatogr., B: Anal. Technol. Biomed. Life Sci.* **2004**, *800*, 49.
26. Smitha, S.; Shajesh, P.; Mukundan, P.; Warriar, K. G. K.; *J. Mater. Res.* **2008**, *23*, 2053.
27. Al-Sagheer, F.; Muslim, S.; *J. Nanomat.* **2010**, *2010*, 7. (doi:10.1155/2010/490679).
28. Stuart, B.; George, W. O.; McIntyre, P. S.; *Modern Infrared Spectroscopy*, John Wiley & Sons: England, 1996.
29. Ogawa, K.; Yui, T.; Okuyama, K.; *Int. J. Biol. Macromol.* **2004**, *34*, 1.
30. Witton, T.; Chareonpanich, M.; Limtrakul, J.; *J. Sol-Gel Sci. Technol.* **2009**, *51*, 146.
31. Neto, C. G. T.; Giacometti, J. A.; Job, A. E.; Ferreira, F. C.; Fonseca, J. L. C.; Pereira, M. R.; *Carbohydr. Polym.* **2005**, *62*, 97.
32. Berger, J.; Reist, M.; Mayer, J. M.; Felt, O.; Peppas, N. A.; Gurny, R.; *Eur. J. Pharm. Biopharm.* **2004**, *57*, 19.
33. Krajewska, B.; *Enzyme Microb. Technol.* **2004**, *35*, 126.
34. Bayramoglu, G.; Meltem, Y.; Arica, M. Y.; *Bioprocess Biosyst. Eng.* **2010**, *33*, 439.
35. Soares, C. M. F.; Santos, O. A.; Olivo, J. E.; de Castro, H. F.; Moraes, F. F.; Zanin, G. M.; *J. Mol. Catal. B: Enzym.* **2004**, *29*, 69.
36. Balcão, V. M.; Paiva, A. L.; Malcata, F. X.; *Enzyme Microb. Technol.* **1996**, *18*, 392.
37. Huang, X. J.; Ge, D.; Xu, Z. K.; *Eur. Polym. J.* **2007**, *43*, 3710.
38. Villeneuve, P.; Muderhwa, J. M.; Graille, J.; Haas, M. J.; *J. Mol. Catal. B: Enzym.* **2000**, *9*, 113.
39. Chiou, S.; Wu, W.; *Biomaterials* **2004**, *25*, 197.
40. De María, P. D.; Sánchez-Montero, J. M.; Alcántara, A. R.; Valero, F.; Sinisterra, J. V.; *Biotechnol. Lett.* **2005**, *27*, 499.

Submitted: November 27, 2010

Published online: March 31, 2011

FAPESP has sponsored the publication of this article.