

# Effectiveness of gutta-percha and Resilon in filling lateral root canals using thermomechanical technique

*Eficácia da gutta-percha e Resilon na obturação de canais laterais usando técnica termomecânica*

Mário TANOMARU-FILHO<sup>a</sup>, Roberta BOSSO<sup>b</sup>, Arnaldo SANT'ANNA-JÚNIOR<sup>b</sup>,  
Fábio Luiz Camargo Villela BERBERT<sup>a</sup>, Juliane Maria GUERREIRO-TANOMARU<sup>a</sup>

<sup>a</sup>Department of Restorative Dentistry, Araraquara Dental School, UNESP – Univ Estadual Paulista,  
14801-903 Araraquara - SP, Brazil

<sup>b</sup>Graduated Student, Department of Restorative Dentistry, Araraquara Dental School,  
UNESP – Univ Estadual Paulista, 14801-903 Araraquara - SP, Brazil

## Resumo

**Objetivo:** O objetivo do estudo foi avaliar a efetividade da gutta-percha e Resilon no preenchimento de canais laterais nos terços cervical, médio e apical radicular quando utilizada a técnica termomecânica. **Material e método:** Canais radiculares de dentes artificiais foram preparados utilizando um método padrão. Canais laterais foram confeccionados utilizando broca com 0,3 mm de diâmetro nos três terços radiculares. Os canais radiculares foram obturados pela técnica híbrida de Tagger utilizando-se o compactador de McSpadden. Foi avaliado o preenchimento dos canais laterais pelos seguintes materiais: cones de gutta-percha Dentsply, gutta-percha Endpoint e Resilon. A avaliação foi realizada por meio da análise de radiografias digitalizadas usando o programa Image Tool. A porcentagem da área preenchida pela área total de cada canal lateral foi determinada. Os dados foram submetidos à análise de variância (ANOVA) e teste de Tukey com nível de significância de 5%. **Resultado:** O Resilon mostrou melhor efetividade como material de preenchimento. Na comparação entre os terços, o Resilon foi mais efetivo no terço apical que no cervical ( $p < 0,05$ ). **Conclusão:** O Resilon foi o material mais efetivo para o preenchimento dos canais laterais quando utilizada a técnica termoplástica.

**Descritores:** Endodontia; gutta-percha; obturação do canal radicular.

## Abstract

**Objective:** The aim of this study was to evaluate the effectiveness of gutta-percha and Resilon in filling lateral root canals in cervical, middle, and apical third using a thermomechanical technique. **Material and method:** Root canals of artificial teeth were prepared using a standard preparation. The lateral canals were fabricated using a 0.3-mm-diameter bur at 3 parts of each root. By using Tagger's hybrid technique with a McSpadden thermomechanical compactor, the root canal was filled using the following filling materials: Dentsply gutta-percha, Endpoint gutta-percha, and Resilon cones. The root canal fillings were evaluated using digitized radiographs and the Image Tool software. The percentage of filled area of each lateral canal was determined. The data were subjected to analysis of variance (ANOVA) and Tukey tests at a 5% significance level. **Result:** Resilon showed better effectiveness as a filling material. When the three thirds were compared, Resilon was more effective in the apical third than in the cervical third ( $p < 0.05$ ). **Conclusion:** Resilon is an effective filling material for lateral root canals using a thermomechanical technique.

**Descriptors:** Endodontics; gutta-percha; root canal filling.

## INTRODUCTION

Endodontic treatment aims to achieve periapical repair by appropriately filling the pulp cavity after cleaning and shaping the root canals<sup>1-6</sup>. The filling technique and the properties of filling material are important factors that influence the three-dimensional filling of the root canal system<sup>7-9</sup>.

An ideal root canal filling should consist of an amount of gutta-percha covered by a thin layer of sealer<sup>10,11</sup>. Therefore,

several filling techniques using thermoplastic gutta-percha have been evaluated for their effectiveness in filling irregular or lateral canals<sup>10,12-18</sup>.

When using thermomechanical techniques for root canal filling, it is important to assess the properties of gutta-percha at high temperatures<sup>19-21</sup>. The thermoplasticity of gutta-percha depends on their chemical composition<sup>19,22,23</sup> and is influenced by

the thermal changes induced during the manufacturing process and during their use<sup>20,22</sup>. Many studies have evaluated several endodontic techniques for their ability to fill a root canal and its irregularities<sup>10,14,16,17</sup>. However, few studies have focused on the thermoplasticity of different brands of gutta-percha when used with thermomechanical techniques<sup>9,13,15,17,24,25</sup>.

Resilon (Resilon Research LLC, Madison, CT, USA), a synthetic polymer-based material, has been proposed as an alternative to gutta-percha<sup>8</sup>. The thermoplastic properties of Resilon were studied by Miner et al.<sup>11</sup> (2006), who showed that Resilon and gutta-percha have a similar melting point of approximately 60 °C. Tanomaru Filho et al.<sup>25</sup> (2007) compared the thermoplastic properties between different gutta-percha cones and Resilon and showed that the latter has higher thermoplasticity.

Several methods have been suggested to promote plasticization of gutta-percha cones. McSpadden's<sup>26</sup> (1978) technique uses a thermomechanical compactor, rotating at a minimum speed of 8,000 rpm, to heat, plasticize, and compact the gutta-percha inside the root canal. In order to achieve better control over the apical limits, Tagger et al.<sup>27</sup> (1984) recommended a hybrid technique that associates lateral condensation in the apical third and thermomechanical compaction in the remaining two-thirds of the root canal.

The thermoplastic properties of filling materials recommended for use with thermomechanical techniques may affect their ability to completely fill the root canal system. Sant'Anna et al.<sup>28</sup> (2009) reported that during thermomechanical compaction, gutta-percha and Resilon present similar temperature-induced changes.

The aim of this study was to assess the ability of different materials (2 different brands of gutta-percha, and Resilon) to effectively fill the artificial lateral canals when used with Tagger's hybrid thermomechanical technique.

## MATERIAL AND METHOD

Thirty transparent resin teeth (Odontofix Indústria e Comércio de Material Odontológico Ltda., Ribeirão Preto, SP, Brazil) were used for the study.

Root canal preparation of the root canals was performed at 1 mm short from the apex by using a rotary system with nickel-titanium files (K3 Endo; Sybron Kerr, Orange, CA, USA). A crown-down technique was used, starting with 0.08-taper files until the apical preparation with a size 35 K3 0.04-taper file. At each file change, the root canals were irrigated with 2 mL distilled water. After instrumentation, the root canals were dried using a size-35 paper cone (Dentsply Indústria e Comércio Ltda., Petrópolis, RJ, Brazil).

The lateral canals were made in the cervical, middle, and apical thirds of the root (4, 8, and 12 mm from the apex) using a cylindrical 0.3-mm bur (ST2 bur; Pluritec, SP, Brazil). An apparatus (Bio-Art Equipamentos Odontológicos Ltda., São Carlos, SP, Brazil) was modified in order to standardize the orientation of the artificial lateral canals. The teeth were randomly divided into 3 groups of 10 specimens, and the root canals were filled with the filling materials being evaluated (Table 1).

The root canal obturation was performed using the Tagger's hybrid technique without endodontic sealer. After placement of the main gutta-percha cone, an endodontic spreader (size-C finger spreader; Dentsply Maillefer, Ballaigues, Switzerland) was used to open space to the insertion of 3 auxiliary cones of the same brand of the main cone. A size-40 thermomechanical compactor (gutta condenser: Dentsply Maillefer), rotating clockwise at 8,000 rpm and penetrating up to 2 mm short of the working length, was used for 10 seconds. The excess root canal filling material was then removed from the pulp chamber.

### 1. Analysis of the Digitized Images

Radiographs of each tooth were obtained in the buccal-lingual position, and then, digitized and standardized using Adobe Photoshop software (Adobe Systems Inc., San Jose, CA, USA). These images were analyzed using the Image Tool software (UTHSCSA Image Tool for Windows version 3.0, San Antonio, TX, USA). The total and filled areas of each lateral canal were measured for all specimens (Figure 1) to determine the percentage of the filled area. The results obtained were then compared at the 3 lateral canals regions (apical, middle, and cervical). The data were subjected to analysis of variance (ANOVA) and the groups were compared using the Tukey test, both at a 5% significance level.

## RESULT

The mean and standard deviation of the percentage of filled area in the different regions of the lateral canal in the 3 experimental groups are shown in Figure 2. Statistical analysis showed that Resilon was the more effective filling material, followed by Endpoint gutta-percha in the 3 evaluated regions of the root ( $p < 0.05$ ). Resilon showed better filling effectiveness in the apical third than in the cervical third ( $p < 0.05$ ); the other 2 materials showed no difference in their filling abilities between the different regions of the root.


## DISCUSSION

Root canal filling techniques using thermoplastic gutta-percha as filling material allow a homogeneous mass that fills the irregularities of the root canal<sup>9,24</sup>. These techniques rely on the thermoplastic properties of gutta-percha, which may vary among the different types and commercial brands of gutta-percha<sup>9,24</sup>.


In this study, artificial lateral canals were prepared using a bur with 0.3 mm diameter. The aim of this study was to compare the

**Table 1.** Filling materials used in the different experimental groups

Group	Material and manufacturer
G1	Gutta-percha Dentsply Termoplástica (Dentsply Indústria e Comércio Ltda., Petrópolis, RJ, Brazil)
G2	Gutta-percha Endpoints Termoplástica (Endpoints Indústria E Comércio Ltda. Paraíba do Sul, RJ, Brazil)
G3	Resilon (Resilon – Pentron Clinical Technologies, Wallingford, PT, USA)

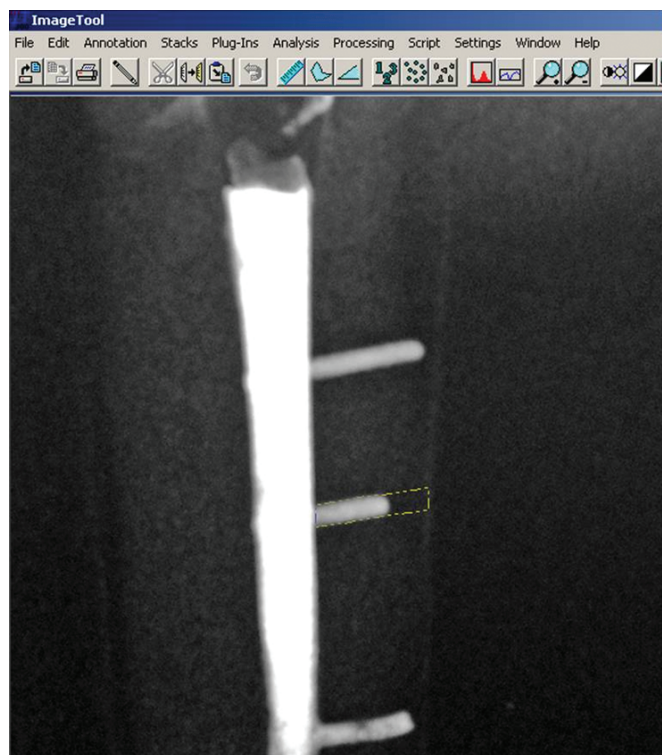

**Figure 1.** Measurement of the filled area of the lateral canal.

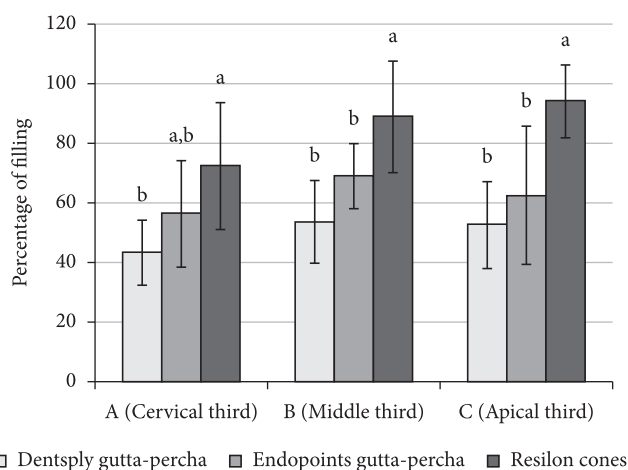

**Figure 2.** Means and Standard Deviation in percentage of the filled areas in the lateral canals, in the different experimental groups and different thirds of the root canal. Means with the same letter (a, b) did not show statistically significant differences ( $p > 0.05$ ).

plasticity of solid root canal filling materials (gutta-percha and Resilon) without using endodontic sealers. The prepared lateral canals allowed the evaluation of the lateral canal filling ability of different root canal filling materials. Compared to the other 2 brands of gutta-percha, Resilon had better lateral canals filling ability using the thermomechanical technique ( $p < 0.05$ ).

The differences observed between the 2 commercial brands of gutta-percha are in agreement with the findings of Gurgel-Filho et al.<sup>24</sup> (2006), who compared the effectiveness of 5 different brands of gutta-percha to fill lateral canals by using a thermomechanical technique and vertical condensation. They concluded that different brands of gutta-percha can present different results when used as a filling material. Gutta-percha is a natural polymer that undergoes industrial processing before being

applied in dentistry. The thermoplastic properties of gutta-percha directly depend on its composition, and are more pronounced in the native gutta-percha than in its processed form<sup>19</sup>. Previous studies have reported that the amount of inorganic elements added to gutta-percha as well as the thermal changes induced during cone manufacturing may affect its properties<sup>22,24</sup>.

Tanomaru-Filho et al.<sup>25</sup> (2007) evaluated the thermoplastic properties of gutta-percha and Resilon, and observed that the latter had higher values ( $p < 0.05$ ). Endpoints (Endpoints Indústria e Comércio Ltda., Paraíba do Sul, RJ, Brazil) had the highest thermoplasticity values, and the values significantly differed from those of the other commercial brands of gutta-percha cones ( $p < 0.05$ ). These findings are in accordance with the present study with regard to the filling ability of gutta-percha in lateral canals obturated by the thermomechanical technique.

New devices and systems using thermoplasticized gutta-percha as root canal filling material have been developed, as the Obtura II system (Model 823-700; Obtura Spartan, Fenton, MO). In comparison to lateral condensation, this technique has shown better adaptation to the root canal walls<sup>29</sup> and can fill a great number of simulated lateral canals<sup>30</sup>.

The findings of this study are also in agreement with those of Karabucak et al.<sup>31</sup> (2008), who evaluated Obtura II and Calamus systems as filling materials for artificial lateral canals in resin teeth. They compared conventional gutta-percha, Flow 150 gutta-percha (Obtura Spartan, Fenton, MO, USA), and Resilon (Resilon Research LLC, North Branford, CT, USA) and found that the flowability of a material depends more on its own properties than on the mechanical properties of the obturating systems. Resilon showed better flow ability in lateral root canals obturated by simple vertical condensation. Tanomaru-Filho et al.<sup>18</sup> (2011) observed that Resilon and EndoFlow gutta-percha were effective in filling lateral canals by using the Obtura II system.

The ability to fill simulated lateral canals of different techniques and root canal filling materials has been studied using natural<sup>32</sup> or artificial teeth<sup>18,24,31</sup>. The use of artificial teeth can positively or negatively influence the flow properties of the gutta-percha or sealer<sup>15</sup>. However, the resin teeth allow to create a similar root canal preparation and standardized lateral canals<sup>15,18,31</sup>.

Almeida et al.<sup>32</sup> (2007) evaluated decalcified and cleared specimens by radiographic and visual analyses after obturation by using lateral condensation. They observed that the radiographic analysis did not detect lateral canal fillings in 8% of the specimens visualized in the decalcified and cleared teeth. However, Tanomaru-Filho et al.<sup>17</sup> (2012) showed similar results from the radiographic and visual analyses of cleared specimens studying lateral canal filling.

## CONCLUSION

The results of this study support the use of Resilon as a filling material when employing Tagger's hybrid thermomechanical technique. However, additional studies comparing Resilon and gutta-percha are necessary to evaluate the performance of these materials when used with different thermomechanical root canal filling techniques.

## REFERENCES

1. Akman M, Akman S, Derinbay O, Belli S. Evaluation of gaps or voids occurring in roots filled with three different sealers. *Eur J Dent.* 2010;4:101-9. PMID:20396439 PMCID:2853831.
2. Bertacci A, Baroni C, Breschi L, Venturi M, Prati C. The influence of smear layer in lateral channels filling. *Clin Oral Investig.* 2007;11:353-9. PMID:17574482. <http://dx.doi.org/10.1007/s00784-007-0127-y>
3. Venturi M, Di Lenarda R, Breschi L. An ex vivo comparison of three different gutta-percha cones when compacted at different temperatures: rheological considerations in relation to the filling of lateral canals. *Int Endod J.* 2006;39:648-56. PMID:16872460. <http://dx.doi.org/10.1111/j.1365-2591.2006.01133.x>
4. Geurtsen W, Leyhausen G. Biological aspects of root canal filling materials-histocompatibility, cytotoxicity, and mutagenicity. *Clin Oral Investig.* 1997;1:5-11. <http://dx.doi.org/10.1007/s007840050002>
5. Holland R, Manne LN, de Souza V, Murata SS, Dezan Júnior E. Periapical tissue healing after post space preparation with or without use of a protection plug and root canal exposure to the oral environment. Study in dogs. *Braz Dent J.* 2007;4:281-8. <http://dx.doi.org/10.1590/S0103-64402007000400002>
6. Silveira AM, Lopes HP, Siqueira JF Jr, Macedo SB, Consolaro A. Periradicular repair after two-visit endodontic treatment using two different intracanal medications compared to single-visit endodontic treatment. *Braz Dent J.* 2007;18:299-304. PMID:18278299. <http://dx.doi.org/10.1590/S0103-64402007000400005>
7. Gençoğlu N, Oruçoğlu H, Helvacıoğlu D. Apical Leakage of Different Gutta-Percha Techniques: Thermafil, Js Quick-Fill, Soft Core, Microseal, System B and Lateral Condensation with a Computerized Fluid Filtration Meter. *Eur J Dent.* 2007;1:97-103. PMID:19212484 PMCID:2609951.
8. Dultra F, Barroso JM, Carrasco LD, Capelli A, Guerisoli DMZ, Pécora JD. Evaluation of apical microleakage of teeth sealed with four different root canal sealers. *J Appl Oral Sci.* 2006;14:341-5. PMID:19089055. <http://dx.doi.org/10.1590/S1678-77572006000500008>
9. Tagger M, Gold A. Flow of various brands of gutta-percha cones under in vitro thermomechanical compactation. *J Endod.* 1988;14:115-20. [http://dx.doi.org/10.1016/S0099-2399\(88\)80210-3](http://dx.doi.org/10.1016/S0099-2399(88)80210-3)
10. Jarrett IS, Marx D, Covey D, Karmazin M, Lavin M, Gound T. Percentage of canals filled in apical cross sections – an in vitro study of seven obturation techniques. *Int Endod J.* 2004;37:392-8. PMID:15186246. <http://dx.doi.org/10.1111/j.1365-2591.2004.00821.x>
11. Miner MR, Berzins DW, Bahcall JK. A comparison of thermal properties between gutta-percha and a synthetic polymer based root canal filling material (Resilon). *J Endod.* 2006;32:683-6. PMID:16793481. <http://dx.doi.org/10.1016/j.joen.2006.01.008>
12. Barroso JM, Carrasco LD, Capelli A, Guerisoli DMZ, Saquy PC, Pécora JD. Influence of gutta-percha points on the filling of simulated lateral canals. *J Appl Oral Sci.* 2005;13:176-9. PMID:20924545. <http://dx.doi.org/10.1590/S1678-77572005000200016>
13. Moeller L, Wenzel A, Wegge-larsen AM, Ding M, Kirkevang L. Quality of root fillings performed with two root filling techniques. An in vitro study using micro-CT. *Acta Odontol Scand.* 2012;1–8. PMID:23145468. <http://dx.doi.org/10.3109/00016357.2012.715192>
14. Gencoglu N, Yildirim T, Garip Y, Karagenc B, Yilmaz H. Effectiveness of different gutta-percha techniques when filling experimental internal resorptive cavities. *Int Endod J.* 2008;41:836-42. PMID:18822011. <http://dx.doi.org/10.1111/j.1365-2591.2008.01434.x>
15. Carvalho-Sousa B, Almeida-Gomes F, Carvalho PR, Maniglia-Ferreira C, Gurgel-Filho ED, Albuquerque DS. Filling lateral canals: evaluation of different filling techniques. *Eur J Dent.* 2010;4:251-6. PMID:20613912 PMCID:2897857.
16. Venturi M. An ex vivo evaluation of a gutta-percha filling technique when used with two endodontic sealers: analysis of the filling of main and lateral canals. *J Endod.* 2008;34:1105-10. PMID:18718375. <http://dx.doi.org/10.1016/j.joen.2008.06.017>
17. Tanomaru-Filho M, Sant'Anna Junior A, Berbert FLCV, Bosso R, Guerreiro-Tanomaru JM. Ability of gutta-percha and Resilon to fill simulated lateral canals by using the Obtura II System. *J Endod.* 2012;38:676–9. PMID:22515901. <http://dx.doi.org/10.1016/j.joen.2012.01.007>
18. Tanomaru-Filho M, Sant'Anna-Junior A, Bosso R, Guerreiro-Tanomaru JM. Effectiveness of gutta-percha and Resilon in filling lateral root canals using the Obtura II System. *Braz Oral Res.* 2011;25:205-9. PMID:21670852. <http://dx.doi.org/10.1590/S1806-83242011000300003>
19. Kolokuris I, Arvanitoyannis I, Blanshard JMV, Robinson C. Thermal analysis of commercial gutta-percha using differential scanning calorimeter and dynamic mechanical thermal analysis. *J Endod.* 1992;18:4-9. [http://dx.doi.org/10.1016/S0099-2399\(06\)81134-9](http://dx.doi.org/10.1016/S0099-2399(06)81134-9)
20. Tanomaru-Filho M, Silveira GF, Reis JMSN, Bonetti-Filho I, Guerreiro-Tanomaru JM. Effect of compression load and temperature on thermomechanical tests for gutta-percha and Resilon. *Int Endod J.* 2011;44:1019–23. PMID:21790663. <http://dx.doi.org/10.1111/j.1365-2591.2011.01910.x>
21. Tanomaru-Filho M, Silveira GF, Tanomaru JM, Bier CA. Evaluation of the thermoplasticity of different gutta-percha cones and Resilon. *Aust Endod J.* 2007;33:23-6. PMID:17461837. <http://dx.doi.org/10.1111/j.1747-4477.2007.00063.x>
22. Zhang C, Huang W, Sun Z, Hou B. A comparison of two gutta-percha master points consisting of different phases in filling of artificial lateral canals and depressions in the apical region of root canals when using a warm vertical compaction technique. *Int Endod J.* 2011;44:1041–6. PMID:21906086. <http://dx.doi.org/10.1111/j.1365-2591.2011.01919.x>
23. Maniglia-Ferreira C, Gurgel-Filho ED, Silva JB Jr, Paula RC, Feitosa JP, Gomes BP, et al. Brazilian gutta-percha points. Part II: thermal properties. *Braz Oral Res.* 2007;21:29-34. PMID:17384852. <http://dx.doi.org/10.1590/S1806-83242007000100005>
24. Gurgel-Filho ED, Feitosa JPA, Gomes BPFA, Ferraz CCR, Souza Filho FJ, Teixeira FB. Assessment of different gutta-percha brands during the filling of simulated lateral canals. *Int Endod J.* 2006;39:113-8. PMID:16454791. <http://dx.doi.org/10.1111/j.1365-2591.2006.01054.x>

25. Tanomaru-Filho M, Bier CA, Tanomaru JM, Barros DB. Evaluation of the thermoplasticity of different gutta-percha cones and the TC system. *J Appl Oral Sci.* 2007;15:131-4. PMID:19089116. <http://dx.doi.org/10.1590/S1678-77572007000200011>
26. McSpadden JT. Self-study course for the thermatic condensation of gutta-percha. Toledo: Ramson & Randolph; 1978.
27. Tagger M, Tamse A, Katz A, Korzen BH. Evaluation of the apical seal produced by a hybrid root canal filling method, combining lateral condensation and thermatic compaction. *J Endod.* 1984;10:299-303. [http://dx.doi.org/10.1016/S0099-2399\(84\)80183-1](http://dx.doi.org/10.1016/S0099-2399(84)80183-1)
28. Sant'Anna-Júnior A, Tanomaru-Filho M, Hungaro Duarte MA, Santos Nunes Reis JM, Guerreiro-Tanomaru JM. Temperature changes in gutta-percha and Resilon cones induced by a thermomechanical compaction technique. *J Endod.* 2009;35:879-82. PMID:19482190. <http://dx.doi.org/10.1016/j.joen.2009.03.009>
29. Weller RN, Kimbrough WF, Anderson RW. A comparison of thermoplastic obturation techniques: adaptation to the canal walls. *J Endod.* 1997;23:703-6. [http://dx.doi.org/10.1016/S0099-2399\(97\)80406-2](http://dx.doi.org/10.1016/S0099-2399(97)80406-2)
30. Goldberg F, Artaza LP, Silvio A. Effectiveness of different obturation techniques in the filling of simulated lateral canals. *J Endod.* 2001;27:362-4. PMID:11485258. <http://dx.doi.org/10.1097/00004770-200105000-00015>
31. Karabucak B, Kim A, Chen V, Iqbal MK. The comparison of gutta-percha and Resilon penetration into lateral canals with different thermoplastic delivery systems. *J Endod.* 2008;34:847-9. PMID:18570993. <http://dx.doi.org/10.1016/j.joen.2008.03.024>
32. Almeida JFA, Gomes BPFA, Ferraz CCR, Souza-Filho FJ, Zaia AA. Filling of artificial lateral canals and microleakage and flow of five endodontic sealers. *Int Endod J.* 2007;40:692-9. PMID:17608677. <http://dx.doi.org/10.1111/j.1365-2591.2007.01268.x>

## CONFLICTS OF INTERESTS

---

The authors declare no conflicts of interest.

## CORRESPONDING AUTHOR

---

Mário Tanomaru-Filho

Department of Endodontics, Araraquara Dental School, UNESP – Univ Estadual Paulista, Rua Humaitá, 1680, 14801-903

Araraquara - SP, Brazil

e-mail: tanomaru@uol.com.br

Recebido: 10/12/2012

Aprovado: 30/01/2013