

Comparative Study of $B_xN_yC_z$ Nanojunctions Fragments

Fabiana Aparecida de Souza Batista^a, Raquel Dastre Manzaneres^a, Magno dos Reis Júnior^a,

Rogério Custódio^b, Ana Claudia Monteiro Carvalho^{a*}

^aGrupo de Desenvolvimento de Estruturas Nanométricas e Materiais Biocompatíveis – GDENB,
Departamento de Física e Química – DFQ, Instituto de Ciências Exatas – ICE,
Universidade Federal de Itajubá – UNIFEI, CEP 37500-930, Itajubá, MG, Brazil

^bInstituto de Química – IQ, Universidade Estadual de Campinas – UNICAMP,
CP 6154, CEP 13084-862, Campinas, SP, Brazil

Received: September 15, 2010; Revised: June 28, 2011

Theoretical analysis of formation energy and geometry was done to compare the relative stabilities of modified carbon nanostructures representative fragments. Structure and energies of formation were calculated at semiempirical level of theory. Depending of B-N pair localization on the molecular structures the formation enthalpy decreases. B-N substitution in tubular structures at low concentration decreases the energy when the tubes have small diameters. Our results are in according to experimental works which have shown that boron and nitrogen are met at region of defects in $B_xC_yN_z$ nanostructures.

Keywords: nanostructures, semiempirical methods, doping, boron, nitrogen

1. Introduction

Carbon nanotubes are considered ideal candidates to the development of nanoelectromechanical (NEMS) devices due the outstanding electronic properties which depend only on their diameter and chirality¹. Researchers have been done to improve growth techniques of carbon nanotubes pure and structurally perfects. On the other hand, the scientific literature has shown a special interest in the development of experimental techniques which could control the growing of branching and/or doping structures. Boron and nitrogen atoms are considered as natural candidates to the doping process²⁻¹⁰.

New growth techniques of Y, L, T, H or multi-branching¹¹⁻²⁰ junctions constituted by nanotubes with the same chirality (or not) made researches about intermolecular junctions which increase the possibilities to built nanodevices based on carbon nanotubes (Figure 1).

Theoretically, nanojunctions can be produced through introduction of topological defects in the tubular structure. Pentagonal, heptagonal, and octagonal rings are examples of this type of defect. According to Euler rule, it is necessary 12 pentagons to close one hexagonal network. However, if we introduce one heptagon, the number of pentagons increases to 13. Moreover, if pentagonal and heptagonal rings are separated by one or more hexagons, we can create nanojunctions with different shapes¹.

Some studies have shown that heteroatoms (as boron and nitrogen) are met in defective regions of tubes²¹. In the case of nitrogen doping nanotubes, there are two results due the inclusion of this heteroatom: (i) the lone pair repulsion decreases the bond angle between nitrogen and carbon atoms which brings on structural stabilization; (ii) one pentagon with nitrogen simulates a carbon hexagon due the extra electron in the nitrogen atom which stabilizes the electronic structure of joint region²²⁻²³.

Emission mechanisms, conduction, and rectification processes are not understood if they are measure from carbon nanostructures. Relationship between morphology and electronic properties show

controversial experimental results which difficult the development of new nanodevices based on nanostructures²⁴⁻³⁰.

In this sense, we made a comparative study of the energy involved in the carbon atom substitution in $B_xN_yC_z$ nanojunctions fragments to propose some rules about the localization of nitrogen and boron atoms in nanojunctions regions of defects.

In the following section we describe the model systems and the theory employed in this study. Next we present a discussion of the results. A final section contains the conclusions.

2. Computational Details

Different semiempirical or hybrid calculations (e.g. ONION)³¹ have been used to nanotube geometry description. Ab initio calculations in Hartree-Fock (HF)³² or Density Functional (DFT)³³ level have been used for low dimension structures.

In this work, the geometry of pure or doped nanotube fragments were fully optimized through semi-empirical quantum chemical methods Austin Method 1 (AM1)³⁴ and Parametric Method 3 (PM3)³⁵. These semi-empirical methods are derived from the Hartree-Fock theory. The advantages of semiempirical calculations are that they are much faster than ab initio calculations, and can be used for large organic molecules. The disadvantage of semiempirical calculations is that some properties cannot be predicted reliably. In the case of the properties analyzed in this study, both semiempirical methods (AM1 and PM3) are very reliable to predict molecular geometries and heats of formation of carbon materials. AM1 and PM3 error in heats of formation is about 8.0 Kcal.mol⁻¹^[36], with respect to the experimental values. Average error in bond length varies from 0.04 Å to 0.05 Å^[36].

Carbon nanojunctions fragments analyzed in this work are shown in Figure 2. The dangling bonds at the ends of the model molecules were saturated with hydrogen (H) atoms. Initially, we calculate the geometries and heats of formation of carbon nanojunction fragments.

*e-mail: anaclaudia@unifei.edu.br

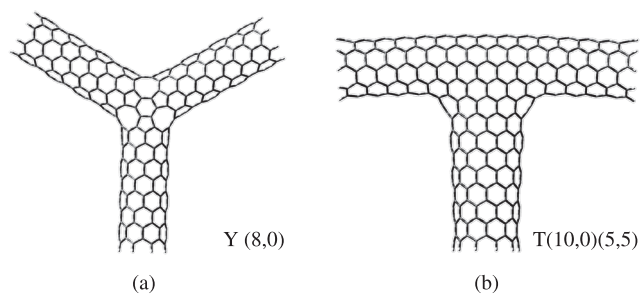


Figure 1. Examples of nanojunctions: a) $Y_{(8,0)}$ formed by three (8,0) semiconducting nanotubes and connected by six pentagons and six octagons; b) $T_{(10,0)(5,5)}$ formed by one metal (5,5) and one semiconducting (10,0) nanotubes. This T-junction has in your defect region four heptagonal rings.

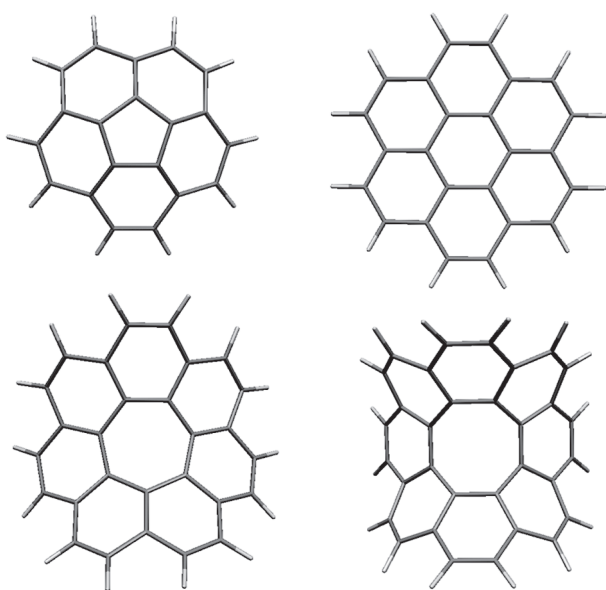


Figure 2. Model molecules geometries calculated through AM1 semiempirical method. In this picture carbon atoms (C) are in gray color and hydrogen atoms (H) are in white color (It was considered structures constituted by one pentagon and five hexagons (PENT), seven hexagonal rings (HEXA), one heptagon and seven hexagons (HEPT), and one octagonal ring rounded by hexagons (OCT)).

These model molecules were then doped with a Boron-Nitrogen pair (BN-pair) and the geometries were re-optimized. Nitrogen (N) and boron (B) atoms were systematically placed substituting carbons in pentagonal, hexagonal, heptagonal, and octagonal rings. For these substitutions, we adopted the following criteria: (i) adjacent B-B or N-N atoms should not be substituted; (ii) the substitution of even number of atoms is preferable because a closed shell system is formed. The results of heat of formation after BN-pair substitution are shown in Table 2. These calculations were performed within the quantum chemical packages GAMESS³⁷ and Gaussian03³⁸.

3. Results and Discussions

3.1. Structural properties and enthalpy of formation

Model molecules are depicted in Figure 2. The selected molecules have five, six, seven and eight-membered rings which are rounded by hexagonal rings.

These fragments have been taken because they are met in some nanojunctions described in the literature³⁸⁻⁴¹. After geometry and formation energy calculations of pure carbon nanostructures, a systematic substitution of carbon atoms by BN-pair was done.

The objective of this study was to identify some rules about the localization of nitrogen and boron atoms in nanojunctions regions of defects. In this sense, we analyzed the theoretical results of the energy associated to BN-pair incorporation. This energy was calculated as the difference in formation enthalpy of BN-pair doped and pure carbon systems divided by the number of BN-pairs. Comparing theoretical results of the enthalpies of formation before and after the substitution of carbon atoms, we concluded that some BN-pair distributions are more desirable than other. In the case of small fullerenes some works have suggested some low energy configurations^{42,43}.

Results for the heat of formation calculated through AM1 semiempirical method are shown in Table 1.

In Table 1 fragments constituted by one pentagon rounded by five hexagons are called PENT; HEPT corresponds to a seven-membered ring rounded by seven hexagons; model molecules with one octagonal ring is called OCT; and model molecules with seven hexagonal rings are called HEXA. Numbers from one to six corresponds to different BN-pair positions. Equivalent substitutions, due the model molecules symmetry, were avoided.

At first, we analyzed the geometry of optimized structures. Model molecules have high curvatures, with exception of ones in the HEXA group. These results are in according to the defective regions met in nanojunctions. Non-hexagonal rings join nanotubes with different chiralities creating different branched structures.

Our analysis of enthalpy of formation for molecules doped with one BN-pair showed that most probable site of these atoms is in the join region of nanojunctions. As closer as boron and nitrogen are one another, lower is that energy (see PentBN_6, PentBN_5, HeptBN_6 in Figure 1 and Table 1). In the case of bonded boron and nitrogen atoms, the better position is nitrogen in the central region and boron in the peripheral region of model molecule. In the case of two BN-pairs, non-carbon atoms need to be located in the central region of defect. Our theoretical results for some model molecules show that the heat of formation decreases with the inclusion of more BN-pairs (compare PentBN_5 with Pent2BN_5, and OctBN_3 with Oct2BN_3).

Since the discovery of $B_xC_yN_z$ nanotubes in 1994⁴⁴, several experimental⁴⁵⁻⁵⁷ and theoretical⁵⁸⁻⁶⁶ works have been done to understand of the properties of this new material. Theoretical studies have revealed that the electronic properties of $B_xC_yN_z$ nanotubes are unrestricted by geometrical structure and can be controlled by simply varying the chemical composition^{61,67,68}.

Golbert et al. reported that multiwalled BN nanotubes have preferentially zigzag type chirality along their circumference based on their diffraction patterns⁴. Other theoretical calculations were performed for the zigzagged form of $B_xC_yN_z$ nanostructures^{69,70}. Therefore, we adoptade only zigzag nanotubes (6,0), (7,0), (8,0), and (9,0) to analyze substitution of BN-pair in tubular structures (Figure 3). In these calculations, BN concentrations are lower than 1%.

Our previous works showed that incorporation of nitrogen zigzag nanotubes stabilizes some geometries^{22,23}. In the case of carbon atoms substitution by boron and nitrogen atoms, our theoretical results showed that BN-pair substitution depends on the tube diameter. Stressed small diameter tubes are more easily doped by BN-pair than the larger ones. Differently of other works⁷¹, our theoretical results show that the relative positions of boron and nitrogen in the tubular wall are not important to the formation energy. Results about

Table 1. Results to Heat of Formation and dipole moment to fragments studied in this work (Figure 1). In this Table molecules constituted by one pentagon rounded by five hexagons are called PENT; HEPT corresponds to a seven-membered ring rounded by seven hexagons; model molecules with one octagonal ring is called OCT; and model molecules with seven hexagonal rings are called HEXA.

Molecule	Heat of formation (Kcal.mol ⁻¹)	Dipole (Debye)	Molecule	Heat of formation (Kcal.mol ⁻¹)	Dipole (Debye)
HEPT			PENT		
Hept C	160.136	0.000	Pent C	156.557	2.796
Hept BN1	202.453	5.251	Pent BN1	180.063	4.689
Hept BN2	157.108	1.014	Pent BN2	199.436	5.426
Hept BN3	159.145	1.951	Pent BN3	161.618	3.122
Hept BN4	208.971	4.461	Pent BN4	377.646	7.642
Hept BN5	146.694	1.444	Pent BN5	149.483	4.456
Hept BN6	145.486	2.513	Pent BN6	141.036	2.377
Hept 2BN1	188.383	3.168	Pent 2BN1	124.440	2.836
Hept 2BN2	155.618	2.229	Pent 2BN2	–	–
Hept 2BN3	270.580	9.639	Pent 2BN3	–	–
Hept 2BN4	220.832	1.492	Pent 2BN4	210.028	3.072
Hept 2BN5	210.685	7.781	Pent 2BN5	129.411	1.960
Hept 2BN6	–	–	Pent 2BN6	142.334	3.718
			Pent 2BN7	216.457	8.044
			Pent 2BN8	231.519	7.103
HEXA			OCT		
Hexa C	96.227	0.000	Oct C	219.678	0.000
Hexa BN1	142.897	5.706	Oct BN1	274.777	8.281
Hexa BN2	151.738	5.658	Oct BN2	274.398	3.920
Hexa BN3	102.802	1.894	Oct BN3	213.489	0.923
Hexa BN4	94.520	1.698	Oct BN4	204.497	1.333
Hexa BN5	92.434	0.990	Oct BN5	262.622	4.047
Hexa 2BN1	74.201	1.660	Oct BN6	274.614	5.286
Hexa 2BN2	69.479	2.368	Oct 2BN1	276.609	1.058
Hexa 2BN3	89.861	0.000	Oct 2BN2	207.666	1.010
Hexa 2BN4	89.028	0.000	Oct 2BN3	186.432	0.000
Hexa 2BN5	118.708	3.454	Oct 2BN4	300.946	4.457
Hexa 2BN6	79.305	0.000	Oct 2BN5	192.072	2.604
			Oct 2BN6	180.021	1.418
			Oct 2BN7	213.435	3.883

Numbers from one to six corresponds to different BN-pair positions.

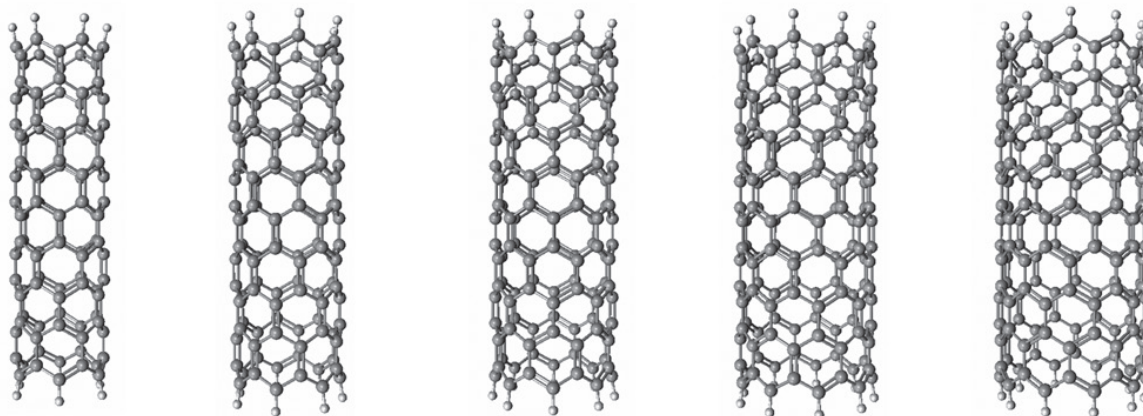


Figure 3. Longitudinal view of zig-zag carbon nanotubes. From left to right: nanotubes (6,0), (7,0), (8,0), (9,0), and (10,0), respectively. All structures were optimized through semiempirical method AM1 (see text).

Table 2. Results for Heat of Formation calculated before and after BN-pair substitution.

Nanotube	Heat of formation (Kcal.mol ⁻¹)	
	AM1	PM3
(6,0)	1542.84	1360.98
(6,0) BN1	1516.73	1314.85
(6,0) BN2	1516.70	1314.83
(6,0) BN3	2822.67	–
(6,0) BN4	1516.70	1314.83
(7,0)	1456.89	1273.41
(7,0) BN1	1469.34	1267.22
(7,0) BN2	1469.38	1267.05
(7,0) BN3	1469.39	1266.85
(7,0) BN4	–	–
(8,0)	1459.47	1269.42
(8,0) BN1	1441.04	–
(8,0) BN2	1457.87	–
(8,0) BN3	–	–
(8,0) BN4	1444.19	1233.36
(8,0) BN5	1457.96	–
(9,0)	1447.61	1249.69
(9,0) BN1	1450.23	1229.75
(9,0) BN2	1450.23	1230.34
(9,0) BN3	1450.72	1230.14
(9,0) BN4	1450.88	1229.58
(9,0) BN5	–	1230.37
(10,0)	–	1232.85
(10,0) BN1	–	1233.04
(10,0) BN2	–	1233.05
(10,0) BN3	–	1232.71
(10,0) BN4	–	1232.92
(10,0) BN5	–	1233.38

BN-pair energy substitution to zigzag nanotubes at concentration higher than 1% have been analyzed (Table 2).

4. Conclusions

In this theoretical work, it has been analyzed the geometry and enthalpy of formation of zig-zag nanotubes and representative fragments of the join region in nanojunctions, through quantum chemical methods.

The geometry of carbon nanotubes has not yet experimentally measured. AM1 results to tubular structures are in according to currently accepted bond lengths in the order of 1.43 Å (average error of 0.04 Å). This result show that AM1 semiempirical method is adequate to geometry calculations to nanotube, nanojunctions, and model molecules analyzed in this work.

After our calculations we can conclude that: (i) the BN-pair substitution decrease the heat of formation of small diameter tubes. The relative positions of boron and nitrogen in the tubular wall are not important to the results of formation energy; (ii) the heat of formation to the fragments depends on the BN-pair localization in the non-hexagonal rings. Non-carbon atoms need to be closer, and the energy decreases with the inclusion of more BN-pairs.

Acknowledgements

The authors thank the computational support from Centro Nacional de Computação de Alto Desempenho - CENAPAD. This work was supported by brazilian agency Conselho Nacional de Pesquisa - CNPq. The author F. A. S. Batista thanks the financial support from Fundação de Pesquisa e Assessoramento à Indústria – FUPAI –, Fundação de Apoio à Pesquisa de Minas Gerais – FAPEMIG – and Coordenação de Aperfeiçoamento de Pessoal de Nível Superior – CAPES.

References

- Saito R, Dresselhaus G and Dresselhaus MS. *Physical Properties of Carbon Nanotubes*. London: Imperial College Press; 1998. <http://dx.doi.org/10.1142/9781860943799>
- Golberg D, Bando Y, Han W, Kurashima K. and Sato T. Single-walled B-doped carbon, B/N-doped carbon and BN nanotubes synthesized from single-walled carbon nanotubes through a substitution reaction. *Chemical Physics Letters*. 1999; 308:337-342. [http://dx.doi.org/10.1016/S0009-2614\(99\)00591-6](http://dx.doi.org/10.1016/S0009-2614(99)00591-6)
- Satishkumar BC, Govindaraja A, Harikumara KR, Zhangc J-P, Cheethamc AK and Rao CNR. Boron-carbon nanotubes from the pyrolysis of C₂H₂-B₂H₆ mixtures. *Chemical Physics Letters*. 1999; 300:473-477. [http://dx.doi.org/10.1016/S0009-2614\(98\)01398-0](http://dx.doi.org/10.1016/S0009-2614(98)01398-0)
- Golberg D, Bando Y, Kurashima K. and Sato T. Ropes of BN multi-walled nanotubes. *Solid State Communications*. 2000; 116(1):1-6. [http://dx.doi.org/10.1016/S0038-1098\(00\)00281-7](http://dx.doi.org/10.1016/S0038-1098(00)00281-7)
- Ma R and Bando Y. Investigation on the growth of boron carbide nanowires. *Chemistry of Materials*. 2002; 14(10):4403-4407. <http://dx.doi.org/10.1021/cm020630v>
- Dorozhkin P, Golberg D, Bando Y and Dong Z-C. Field emission from individual B-C-N nanotube rope. *Applied Physics Letters*. 2002; 81(6):1083-1085. <http://dx.doi.org/10.1063/1.1497194>
- Trasobares S, Stéphan O, Colliex C, Hsu WK, Kroto HW and Walton DRM. Compartmentalized CN_x nanotubes: Chemistry, morphology, and growth. *Journal of Chemical Physics*. 2002; 116(20):8966-8972. <http://dx.doi.org/10.1063/1.1473195>
- Terrones M, Ajayan PM, Banhart F, Blase X, Carroll DL, Charlier JC. et al. N-doping and coalescence of carbon nanotubes: synthesis and electronic properties. *Applied Physics A: Materials Science & Processing*. 2002; 74:355-360. <http://dx.doi.org/10.1007/s003390201278>
- Yu SS. Nature of substitutional impurity atom B/N in zigzag single-wall carbon nanotube revealed by first-principle calculations. In: *IEEE Transactions on Nanotechnology*; 2006; Changchun. Changchun: Jilin University; 2006. v. 5, p. 595-598.
- Golberg D, Dorozhkin PS, Bando Y, Dong Z-C, Tang CC, Uemura Y et al. Structure, transport and field-emission properties of compound nanotubes : CN_x vs BNC_x (x < 0.1). *Applied Physics A: Materials Science & Processing*. 2003; 76:499-507. <http://dx.doi.org/10.1007/s00339-002-2047-7>
- Piazza F, Nocuaa JE, Hidalgo A, Jesús J, Velázquez R, Weiss BL et al. Formation of boron carbonitride nanotubes from in situ grown carbon nanotubes. *Diamond and Related Materials*. 2005; 14:965-969. <http://dx.doi.org/10.1016/j.diamond.2005.01.024>
- Han J, Anantram MP and Jaffe RL. Observation and modeling of single-wall carbon nanotube bend junctions. *Physical Review B*. 1998; 57:14893-14989. <http://dx.doi.org/10.1103/PhysRevB.57.14983>
- Menon M and Shivastava D. Carbon nanotube based molecular electronic devices. *Journal of Materials Research*. 1998; 13:2357-2362. <http://dx.doi.org/10.1557/JMR.1998.0328>
- Andriotis AN, Menon M, Srivastava D and Chernozatonskii L. Ballistic switching and rectification in single wall carbon nanotube Y junction. *Applied Physics Letters*. 2001; 79:266-268. <http://dx.doi.org/10.1063/1.1385194>

15. Ting J-M, Li T-P and Chang C-C. Carbon nanotube with 2D e 3D multiple junction. *Carbon*. 2004; 42:2997-3002. <http://dx.doi.org/10.1016/j.carbon.2004.07.014>
16. Heyning OT, Berniera P and Glerup M. A low cost method for the direct synthesis of highly Y-branched nanotubes. *Chemical Physics Letters*. 2005; 409:43-47. <http://dx.doi.org/10.1016/j.cplett.2005.04.097>
17. Ting J-M and Chang C-C. Multijunction carbon nanotube network. *Applied Physics Letters*. 2002; 80:324-325. <http://dx.doi.org/10.1063/1.1432442>
18. Ye Y, Ahn CC, Witham C, Fultz B, Liu J, Rinzler AG et al. Hydrogen adsorption and cohesive energy of single-walled carbon nanotubes. *Applied Physics Letters*. 1999; 74:2307-2309. <http://dx.doi.org/10.1063/1.123833>
19. Terrones M, Banhart F, Grobert N, Charlier J-C, Terrones H and Ajayan PM. Molecular junctions by joining single-walled carbon nanotubes. *Physical Review Letters*. 2002; 89:075505-075508. <http://dx.doi.org/10.1103/PhysRevLett.89.075505>
20. Grimm D, Muniz RB and Latgé A. From straight carbon nanotubes to Y-shaped junctions and rings. *Physical Review B*. 2003; 68:193407. <http://dx.doi.org/10.1103/PhysRevB.68.193407>
21. Charlie, J-C, Ebbesen TW and Lambin P. Structural and electronic properties of pentagon-heptagon pair defects in carbon nanotubes. *Physical Review B*. 1996; 53:11108-11113. <http://dx.doi.org/10.1103/PhysRevB.53.11108>
22. Zhang GY, Ma XC, Zhong DY and Wang EG. Polymerized carbon nitride nanobells. *Journal of Applied Physics*. 2002; 91:9324-9332. <http://dx.doi.org/10.1063/1.1476070>
23. Carvalho ACM and Dos Santos MC. Stabilizing Y-junctions and ring structures through nitrogen substitution. *AIP Conference Proceedings*. 2004; 723:347-350. <http://dx.doi.org/10.1063/1.1812104>
24. Carvalho ACM and Dos Santos MC. Nitrogen-substituted nanotubes and nanojunctions: Conformation and electronic properties. *Journal of Applied Physics*. 2006; 100:084305-1-084305-5. <http://dx.doi.org/10.1063/1.2357646>
25. Klusek Z, Datta S, Byszewski P, Kowalczyk P and Kozłowski W. Scanning tunneling microscopy and spectroscopy of Y-junction in carbon nanotubes. *Surface Science*. 2002; 507:577-581. [http://dx.doi.org/10.1016/S0039-6028\(02\)01313-4](http://dx.doi.org/10.1016/S0039-6028(02)01313-4)
26. Liu, H. The influence of defect on quantum conductivity in three-terminated Y-(or T)-junction single-walled carbon nanotube. *Physics Letters A*. 2005; 339:378-386. <http://dx.doi.org/10.1016/j.physleta.2005.03.053>
27. Del Valle M, Tejedor C and Cuniberti G. Defective transport properties of three-terminal carbon nanotube junctions. *Physical Review B*. 2005; 71:125306. <http://dx.doi.org/10.1103/PhysRevB.71.125306>
28. Triozon F, Lambin P and Roche S. Electronic transport properties of carbon nanotube based metal/semiconductor/metal intramolecular junctions. *Nanotechnology*. 2005; 16:230-233. <http://dx.doi.org/10.1088/0957-4484/16/2/008>
29. Liu LW, Fang JH, Lu L, Zhou F, Yang HF, Jin AZ et al. Three-terminal carbon nanotube junctions: Current-voltage characteristics. *Physical Review B*. 2005; 71:155424. <http://dx.doi.org/10.1103/PhysRevB.71.155424>
30. Ding F. Theoretical study of the stability of defects in single-walled carbon nanotubes as a function of their distance from the nanotube end. *Physical Review B*. 2005; 72:245409. <http://dx.doi.org/10.1103/PhysRevB.72.245409>
31. Kar T, Akdim B, Duan X and Pachter R. A theoretical study of functionalized single-wall carbon nanotubes: ONIOM calculations. *Chemical Physics Letters*. 2004; 392:176-180. <http://dx.doi.org/10.1016/j.cplett.2004.05.015>
32. Wanbayor R, Ruangpornvisuti V. Adsorptions of proton, hydroxide on various cap-ended and open-ended armchair (5,5) single-walled carbon nanotubes. *Chemical Physics Letters*. 2007; 441:127-131. <http://dx.doi.org/10.1016/j.cplett.2007.05.005>
33. Petsalakis ID, Pagona G, Tagmatarchis N and Theodorakopoulos G. Theoretical study in donor-acceptor carbon nanohorn-based hybrids. *Chemical Physics Letters*. 2007; 448:115-120. <http://dx.doi.org/10.1016/j.cplett.2007.09.067>
34. Stewart JJP. Optimizaton of Parameters for Semiempirical Methods.1. Method. *Journal of Computational Chemistry*. 1989; 10:209-220. <http://dx.doi.org/10.1002/jcc.540100208>
35. Stewart JJP. Optimizaton of Parameters for Semiempirical Methods. 2. Applications. *Journal of Computational Chemistry*. 1989; 10:221-264. <http://dx.doi.org/10.1002/jcc.540100209>
36. Young DC. *Computational Chemistry: A practical guide for applying techniques to real-world problems*. New York: Wiley-Interscience; 2001.
37. Schmidt MW, Baldrige KK, Boatz JA, Elbert ST, Gordon MS, Jensen JH et al. General Atomic and Molecular Electronic-Structure System. *Journal of Computational Chemistry*. 1993; 14:1347-1363. <http://dx.doi.org/10.1002/jcc.540141112>
38. Frisch MJ, Trucks GW, Schlegel HB, Scuseria GE, Robb MA, Cheeseman JR et al. *Gaussian 03*. Version 6.1. Wallingford: Gaussian, Inc.; 2004.
39. Menon M and Srivastava D. Carbon nanotube "T junctions": Nanoscale metal-semiconductor-metal contact devices. *Physical Review Letters*. 1997; 79:4453-4456. <http://dx.doi.org/10.1103/PhysRevLett.79.4453>
40. Menon M and Srivastava D. Carbon nanotube based molecular electronic devices. *Journal of Materials Research*. 1998; 13:2357-2362. <http://dx.doi.org/10.1557/JMR.1998.0328>
41. Schultz D, Droppa Junior R, Alvarez F and Dos Santos MC. Stability of small carbon-nitride heterofullerenes. *Physical Review Letters*. 2003; 90:015501-015504. <http://dx.doi.org/10.1103/PhysRevLett.90.015501>
42. Kar T, Pattanayak J and Scheiner S. Rules for BN-substitution in BCN-fullerenes. Separation of BN and C domains. *Journal of Physical Chemistry A*. 2003; 107:8630-8637. <http://dx.doi.org/10.1021/jp035744o>
43. Viani L and Dos Santos MC. Comparative study of lower fullerenes doped with boron and nitrogen. *Solid State Communications*. 2006; 138:498-501. <http://dx.doi.org/10.1016/j.ssc.2006.04.027>
44. Stephan O, Ajayan PM, Colliex C, Redlich P, Lambert JM, Bernier P et al. *Science*. 1994; 266:1683. <http://dx.doi.org/10.1126/science.266.5191.1683>
45. Weng-Sieh Z, Cherrey K, Chopra NG, Blase X, Miyamoto Y, Rubio A et al. Synthesis of B_xC_yN_z nanotubules. *Physical Review B*. 1995; 51:11229-11232. <http://dx.doi.org/10.1103/PhysRevB.51.11229>
46. Redlich P, Loeffler J, Ajayan PM, Bill J, Aldinger F and Rühle M. B-C-N nanotubes and boron doping of carbon nanotubes. *Chemical Physics Letters*. 1996; 260:465-470. [http://dx.doi.org/10.1016/0009-2614\(96\)00817-2](http://dx.doi.org/10.1016/0009-2614(96)00817-2)
47. Zhang Y, Gub H, Suenaga K and Iijima S. Heterogeneous growth of B-C-N nanotubes by laser ablation. *Chemical Physics Letters*. 1997; 279:264-269. [http://dx.doi.org/10.1016/S0009-2614\(97\)01048-8](http://dx.doi.org/10.1016/S0009-2614(97)01048-8)
48. Sen R, Satishkumar BC, Govindaraj A, Harikumar KR, Raina G, Zhang J-P et al. B-C-N and B-N nanotubes produced by the pyrolysis of precursor molecules over Co catalysts. *Chemical Physics Letters*. 1998; 287:671-676. [http://dx.doi.org/10.1016/S0009-2614\(98\)00220-6](http://dx.doi.org/10.1016/S0009-2614(98)00220-6)
49. Kim CS, Jeonga SM, Kooa WH, Baik HK, Leeb S-J and Song KM. Synthesis of B-C-N nanotubes by means of gas arc discharge with a rotating anode. *Materials Letters*. 2004; 58:2878-2881. <http://dx.doi.org/10.1016/j.matlet.2004.05.053>
50. Wang WL, Bai XD, Liu KH, Xu Z, Golberg D, Bando Y et al. Direct Synthesis of B-C-N single-walled nanotubes by bias-assisted hot filament chemical vapor deposition. *Journal of the American Chemical Society*. 2006; 128:6530-6531. <http://dx.doi.org/10.1021/ja0606733>
51. Yu J, Ahn J, Yoon SF, Zhang Q, Rusli, Gan B et al. Semiconducting boron carbonitride nanostructures: Nanotubes and nanofibers. *Applied Physics Letters*. 2000; 77:1949-1951. <http://dx.doi.org/10.1063/1.1311953>
52. Bai XD, Guo JD, Yu J, Wang EG, Yuan J and Zhou W. Synthesis and field-emission behavior of highly oriented boron carbonitride nanofibers. *Applied Physics Letters*. 2000; 76:2624-2626. <http://dx.doi.org/10.1063/1.126429>
53. Bai XD, Wang EG, Yu J and Yang H. Blue-violet photoluminescence from large scale highly aligned boron carbonitride nanofibers. *Applied Physics Letters*. 2000; 77:67-69. <http://dx.doi.org/10.1063/1.126879>
54. Yin LW, Bando Y, Golberg D, Gloter A, Li M-S, Yuan X et al. Porous BCN nanotubular fibers: Growth and Spatially resolved cathodoluminescence.

- Journal of the American Chemical Society*. 2005; 127:16354-16355. <http://dx.doi.org/10.1021/ja054887g>
55. Liao L, Liu K, Wang W, Bai X, Wang E, Liu Y et al. Multiwall boron carbonitride/carbon nanotube junction and its rectification behavior *Journal of the American Chemical Society*. 2007; 129:9562-9563. <http://dx.doi.org/10.1021/ja072861e>
56. Golberg D, Bando Y, Han W, Kurashima K and Sato T. Single-walled B-doped carbon, B/N-doped carbon and BN nanotubes synthesized from single-walled carbon nanotubes through a substitution reaction. *Chemical Physics Letters*. 1999; 308:337-342. [http://dx.doi.org/10.1016/S0009-2614\(99\)00591-6](http://dx.doi.org/10.1016/S0009-2614(99)00591-6)
57. Enouz S, Stéphan O, Cochon J-L, Colliex C and Loiseau A. C-BN Patterned Single-Walled Nanotubes Synthesized by Laser Vaporization. *Nano Letters*. 2007; 7:1856-1862. <http://dx.doi.org/10.1021/nl070327z>
58. Choi J, Kim Y-H, Chang KJ and Tománek D et al. Itinerant ferromagnetism in heterostructured C/BN nanotubes. *Physical Review B*. 2003; 67:125421-125425. <http://dx.doi.org/10.1103/PhysRevB.67.125421>
59. Guo CS, Fan WJ, Chen ZH and Zhang RQ. First-principles study of single-walled armchair C_x(BN)_y nanotubes. *Solid State Communications*. 2006; 137:549-552. <http://dx.doi.org/10.1016/j.ssc.2006.01.012>
60. Matos M, Azevedo S and Kaschny JR. On the structural properties of B-C-N nanotubes *Solid State Communications*. 2009; 149:222-226. <http://dx.doi.org/10.1016/j.ssc.2008.11.011>
61. Blase X, Charlier J-C, De Vita A and Car R. Theory of composite B_xC_yN_z nanotube heterojunction. *Applied Physics Letters*. 1997; 70:197-199. <http://dx.doi.org/10.1063/1.118354>
62. Blase X. Properties of composite B_xC_yN_z nanotubes and related heterojunctions. *Computational Materials Science*. 2000; 17:107-114. [http://dx.doi.org/10.1016/S0927-0256\(00\)00006-9](http://dx.doi.org/10.1016/S0927-0256(00)00006-9)
63. Pan H, Feng YP and Lin JY. First-principles study of optical spectra of single-wall BC₂N nanotubes. *Physical Review B*. 2006; 73:035420-035426. <http://dx.doi.org/10.1103/PhysRevB.73.035420>
64. Hernández E, Goze C, Bernie P and Rubio A. Elastic properties of C and B_xC_yN_z composite nanotubes *Physical Review Letters*. 1998; 80:4502-4505. <http://dx.doi.org/10.1103/PhysRevLett.80.4502>
65. Bhattacharya S, Majumder C and Das GP. Hydrogen storage in Ti-Decorated BC₂N nanotube. *Journal of Physical Chemistry C*. 2008; 112:17487-17491. <http://dx.doi.org/10.1021/jp807280w>
66. Kim SY, Park J, Choi HC, Ahn JP, Hou JQ, Seok H et al. X-ray photoelectron spectroscopy and first principles calculation of BCN nanotubes. *Journal of the American Chemical Society*. 2007; 129:1705-1716. <http://dx.doi.org/10.1021/ja067592r>
67. Kawaguchi M. B/C/N materials based on the graphite network. *Advanced Materials*. 1997; 9:615-625. <http://dx.doi.org/10.1002/adma.19970090805>
68. Miyamoto Y, Rubio A, Cohen ML and Louie SG. Chiral tubules of hexagonal BC₂N. *Physical Review B*. 1994; 50:4976-4979. <http://dx.doi.org/10.1103/PhysRevB.50.4976>
69. Moghaddam HM. The CNT/BCN/CNT structure (zigzag type) as molecular switch. *Physica E*. 2009; 42:167-171. <http://dx.doi.org/10.1016/j.physe.2009.10.002>
70. Mirzaei M. Calculation of chemical shielding in C-doped zigzag BN nanotubes. *Monatshefte Für Chemie*. 2009; 140:1275-1278. <http://dx.doi.org/10.1007/s00706-009-0195-6>
71. Wang P and Zhang C. Doped ways of boron and nitrogen doped carbon nanotubes: A theoretical investigation. *Journal of Molecular Structure: THEOCHEM*. 2010; 955:84-90. <http://dx.doi.org/10.1016/j.theochem.2010.06.006>